

Cold-bonding process for treatment and reuse of waste materials: technical designs and applications of pelletized products

Authors: Alberto Ferraro^{a*}, Francesco Colangelo^b, Ilenia Farina^b, Marco Race^c, Raffaele Cioffi^b, Christopher Cheeseman^d, Massimiliano Fabbicino^a

Affiliations:

^a Department of Civil, Architectural and Environmental Engineering, University of Naples “Federico II”, Via Claudio 21, 80125, Naples, Italy

^b Department of Engineering, University of Naples “Parthenope”, Centro Direzionale di Napoli, Isola C4, 80143, Naples, Italy

^c Department of Civil and Mechanical Engineering, University of Cassino and Southern Lazio, Via di Biasio 43, 03043, Cassino, Italy

^d Department of Civil and Environmental Engineering, Imperial College London, South Kensington, London, SW7 2BU, UK

*** Corresponding Author:** Alberto Ferraro (alberto.ferraro3@gmail.com)

Journal: Critical Reviews in Environmental Science and Technology

21	Table of contents
22	Abstract
23	1. Introduction
24	2. Cold-bonding processing
25	3. Mix-design for cold-bonding pelletization
26	3.1 Mix-design for pellets using fly-ash as waste material
27	3.2 Mix-design for pellets with ore tailings as waste material
28	3.3 Mix-design for pellets with different waste materials
29	4. Parameters affecting the cold-bonding process efficiency
30	5. Application of the cold-bonded pellets
31	5.1 Cold-bonded pellets as aggregates for lightweight concrete
32	5.2 Cold-bonded pellets as aggregates for self-compacting concrete
33	5.3 Cold-bonded pellets for less investigated applications
34	6. Conclusions
35	Acknowledgements
36	References

37

38

39

40

41

42

Abstract

This work provides a comprehensive review of research on the cold-bonding pelletization process used to produce lightweight aggregates (LWAs) using waste materials, to valorise the waste and, at the same time, minimize risks related to disposal. Research investigating various aspects of the cold-bonding process highlight: i) feasible mix-designs for pellet production; ii) the most relevant operating parameters affecting the process; and iii) the potential applications of the LWAs produced. The analysis gives a wide overview of the fundamental key-points that control the cold-bonding process. Data comparison provides a useful way to identify the optimal process conditions to allow development of optimum products. This involves the selection of the correct mix-design, including suitable binders and potential additives, and the selection of appropriate operating conditions, which are a function of the waste investigated, and/or waste mix characteristics. The review proposes an optimised approach to experimental studies on cold-bonding processes that has potential to enhance future process performance. Moreover, the present work provides a complete framework useful for decision-making for both manufacturers and researchers working to use this promising technique.

Key words: Cold-bonding process; Pelletization efficiency; Lightweight aggregates; Lightweight concrete; Aggregate mix-designs

1. Introduction

Stabilization/solidification (S/S) has been widely used in the last few decades on many types of waste materials as a remediation solution, which allows pollutant containment and prevents leaching of hazardous compounds (Senneca et al., 2020). While the initial applications of S/S were focused on the production of a stabilized waste for environmentally safe disposal, it is now being used as a technology to allow the possible reuse of stabilized waste products as aggregates to be used in the construction industry (Colangelo, Cioffi, Montagnaro, & Santoro, 2012; Narattha & Chaipanich, 2018). An interesting application of this is the manufacture of artificial lightweight aggregates (LWA) (Ayati, Ferrándiz-Mas, Newport, & Cheeseman, 2018; Velis et al., 2014). LWA can be produced through pelletization which is an agglomeration phenomena that occurs to moist waste fines containing a binder (Baykal & Döven, 2000). The pelletized LWA product can then be obtained by sintering, which involves heating the aggregates after pelletization, or by cold-bonding which allows LWA pellets to form at ambient temperature (Ayati, Molineux, Newport, & Cheeseman, 2019; Bui, Hwang, Chen, & Hsieh, 2012). Despite the rapid production of a readily usable product by sintering, the high temperatures (900-1400 °C) needed are a disadvantage compared to the cold-bonding process which requires less energy consumption and reduces secondary pollution formation (Thomas & Harilal, 2015). In recent years several studies have investigated cold-bonding pelletization processes to determine optimal operating conditions (Frankovič, Bosiljkov, & Ducman, 2017; Gesoğlu, Güneyisi, & Öz, 2012). These have determined suitable mix-designs for the production of LWA with appropriate properties. It is evident that the final characteristics of the stabilized products have wide variability depending on numerous factors affecting the process. From this perspective, the present work aims to provide a comprehensive and technical overview of scientific studies focused on cold-bonding pelletization reported in the scientific literature. This can provide a significant contribution by analysing and identifying useful and

complete information to support the operational practices of both researchers and industrial manufacturers working on the cold-bonding process. For this aim, this work focuses on studies concerning the effect of operating parameters on the process performance including the waste/binder ratio, the waste properties, angle and rotation speed of the pelletizer, the process duration, and the aggregate curing method. Finally, studies related to the possible applications of pelletized materials are analysed to highlight the benefits resulting from using cold-bonding processes.

2. Cold-bonding processing

The cold-bond process uses a rotating plate, which causes pellet formation for moist materials because of the plate rotation effect. This allows the formation of granular structures with enhanced bonding forces due to centrifugal and gravitational forces (Arslan & Baykal, 2006). The pelletization process is characterized by three stages. These are the i) the pendular state (water on the grains contact point), ii) the funicular state (water filling some pores) and, iii) the capillary state (water filling all intergranular spaces) which represents the best pelletization condition (Baykal & Döven, 2000). The first step of the pelletization process is represented by the mixture wetted by water addition. The nucleation phase allows formation of granule nuclei, which are loosely packed. Depending on the agitation intensity and granule nuclei resistance, the consolidation phase can take place through collisions of different nuclei. During collisions, the granules bond to form larger particles by coalescence. Strong bond formation among granules should occur in order to achieve efficient particle formation (Hapgood, Iveson, Litster, & Liu, 2007).

The pelletization process is mainly driven by gravitational/centrifugal forces. Operating parameters that control the process are the rotation velocity and inclination of the pelletizer

plate as well as the amount of water in the mix. These parameters will be discussed in more detail.

The overall processing scheme is summarized in Fig. 1. The main element of the pelletizer is the rotating plate and this exerts the rotation effect on the mix particles. A speed regulator adjusts the rotational velocity of the plate, while plate inclination can also be controlled. Water addition can be performed either manually or in automated mode. In this latter case, the pelletizer is equipped with a nebulizer and related nozzles for spraying water on the mixture. Moreover, one or more scrapers is generally placed in different positions on the rotating plate. The scrapers are used to remove the material adhering to both the surface and side of the rotating plate to avoid unused particles in the process.

3. Mix-design for cold-bonding pelletization

3.1 Mix-design for pellets using fly-ash as waste material

Coal and municipal solid waste incineration fly-ashes (FA) are probably the waste materials most frequently used in the cold-bonding pelletization process (Table 1) because of the large available amount of these wastes which can be stabilized/solidified and used as aggregate (G. Joseph & Ramamurthy, 2009a). Cold-bonded aggregates made from FA have mechanical properties similar to commercial LWAs (Rivera, Martínez, Castro, & López, 2015). However, the correct mix-design to achieve good results is challenging, with LWA properties strongly depending on the FA chemical composition. For example, high CaO content may lead to reduced crushing strengths of LWA pellets (Gesoğlu, Özturan, & Güneyisi, 2007).

Cold-bonded pellets prepared using just FA have low quality compared to pellets produced using additional binders (Baykal & Döven, 2000), particularly in terms of compressive strength, specific gravity and water absorption capacity. Similarly, cold-bonded pellets prepared using

139 mechanically activated FA mixed with Na_2SiO_3 have much worse mechanical properties (about
140 50% lower), compared to sintered pellets prepared using the same mix-design (Terzić, Pezo,
141 Mitić, & Radojević, 2015). The same occurs for cold-bonded pellets prepared using FA alkali
142 activated with NaOH and mixed with bentonite (Gomathi & Sivakumar, 2015). Cold-bonded
143 pellets produced using FA and phase change materials (PCM) had poor properties, particularly
144 as the percentage of PCM in the mix increased (Tuncel & Pekmezci, 2018).

145 Improved performance of cold-bonded pelletized FA aggregates was obtained by adding
146 Portland cement (Arslan and Baykal, 2006). FA pellets also increased in specific gravity, bulk
147 unit weight and particle strength and the water absorption capacity decreased when the cement
148 addition increased from 10 to 20% (Chi et al., 2003).

149 The addition of $\text{Ca}(\text{OH})_2$ to FA pellets can also produce pellets with good characteristics,
150 although the samples formed were not as good in terms of pellet density, water absorption and
151 crushing strength as samples made using cement. Further additions of $\text{Ca}(\text{OH})_2$ reduced the
152 quality of the pellets formed (Narattha & Chaipanich, 2018).

153 The addition of more components in the cold-bonded pellet mix-design may change the
154 properties. For example, the three-component mixture containing FA, cement and granulated
155 blast furnace slag (GGBS) and the three-component mixture containing, FA, cement and rice
156 husk ash (RHS) have been investigated. These had very different properties. The crushing
157 strength was much higher for pellets containing GGBS compared to pellets containing RHS
158 (Bui, Hwang, Chen, & Hsieh, 2012). This is because the GGBS is alkali activated and this
159 produces additional C-S-H, the main binding phase in cementitious materials. The GGBS
160 samples also had decreased water absorption, due to the higher density of the aggregate
161 microstructure associated with increased formation of C-S-H gel (Bui, Hwang, Chen, & Hsieh,

2012). The positive effects of GGBS compared to RHS were also observed for cold-bonded pellets produced using two-component mixtures without cement.

An increase of strength, absorption capacity and unit weight is reported with increasing GGBS content in a two-component mix containing FA+GGBS (from 15.5 to 15.7 MPa, from 7.8 to 8.3%, from 1003 to 1060 kg m⁻³, respectively). For the two-component mixtures containing FA+RHS, values of strength, absorption capacity and unit weight varied in a range from 6 to 8.1 MPa, from 10.8 to 20.5%, and from 833 to 769 kg m⁻³, respectively. Improved enhancement in properties is also observed compared to the three-component mixtures containing both GGBS and RHS with FA (from 8.1 to 8.8 MPa, from 9.8 to 10.1%, from 855 to 894 kg m⁻³, respectively) (Bui, Hwang, Chen, Lin, & Hsieh, 2012).

The partial replacement of FA (up to 40%) with expanded perlite powder also produces an important improvement in aggregate mechanical properties (Tajra, Elrahman, Chung, & Stephan, 2018). Similarly, the partial replacement of FA with bentonite or kaolinite may improve the mechanical characteristics of cold-bonded pellets. This clearly indicates the beneficial effects on process performances through the use of clay minerals (Manikandan & Ramamurthy, 2007). It is reported that high swelling bentonite leads to a higher pelletization efficiency compared to medium swelling bentonite at the same dosage. This is due to the higher amount of interlayer cations in the high swelling bentonite causing the formation of more expanded montmorillonite platelet fibres available for the attraction FA particles (Manikandan & Ramamurthy, 2009).

Improved mechanical strength and water absorption capacity are observed using an aggregate mixture containing FA+furnace slag, alkali activated using NaOH solution (Gomathi & Sivakumar, 2014). In this case, a crushing strength of 22.8 MPa, and a water absorption capacity of 13.0% were observed. The latter values are preferable compared to the crushing strength of

14.5 MPa and to the water absorption capacity of 16.4% obtained using a mixture alkali activated of FA+bentonite, or 17.6 MPa, and 17.9% observed for mixture alkali activated of FA+metakaolin. Similar results are obtained for this two-component mixture using other alkali activators (Yliniemi, Nugteren, et al., 2016; Yliniemi, Tiainen, & Illikainen, 2016). However the use of sodium silicate may not avoid leaching of anionic complexes of heavy metals in the stabilized pellets (Yliniemi, Pesonen, et al., 2016).

The partial replacement of FA with different wastes for cold-bonded pellets production can be beneficial not only in terms of process efficiency, but also as a way to recycle waste. Tang & Brouwers (2017) report an overall improvement of pellets properties through the addition of different components such as bottom ash (BA) fines, paper sludge ash (PSA), and polypropylene fibre (PPF) to the aggregates mixture. LWA pellets production used different mixtures of weathered FA, wastewater treatment sludge and desulfurization device sludge with lime addition (Ferone et al., 2013). Indeed, binary mixtures of weathered FA+wastewater treatment sludge or desulfurization device sludge, and ternary mixture of the same materials show feasible properties for LWA production.

Hwang & Tran (2015) analysed the effect of hydrogen peroxide as foaming agent for the production of foamed LWA from binary mixture of FA+GGBS and ternary mixture of FA+GGBS+cement. Despite the positive effect on foamed LWA properties with optimal hydrogen peroxide percentage (7%), results show decreasing values of crushing strength with increasing hydrogen peroxide concentrations for both FA+GGBS (80%+20%, respectively) and FA+GGBS+cement (70%+20%+10%, respectively) mixtures. A further study focused on the production of geopolymer aggregates from fluidized bed combustion FA and mine tailing material (Yliniemi, Paiva, Ferreira, Tiainen, & Illikainen, 2017). In this case, results displayed better mechanical properties of FA geopolymer aggregates due to the higher crushing force required compared to the mine tailing geopolymer aggregates.

Finally, Colangelo, Messina, & Cioffi (2015), implemented a double step cold-bonding process for pellets production using municipal solid waste incineration (MSWI) FA from rotary and stoker furnaces. In this case, tests were carried out on different mixtures containing MSWI FA+cement, MSWI FA+lime, and MSWI FA+coal FA, subjected to a second pelletization step using a 1:1 cement/coal FA binder. This approach increased the mechanical properties of the produced cold-bonded pellets, reducing, at the same time, the risk of metal leaching which can be significantly consistent for the MSWI FA (Ferraro et al., 2019).

3.2 Mix-design for pellets with ore tailings as waste material

The cold-bonding technique has been widely applied for the stabilization/solidification of ore fines tailings produced by mining and milling activities (Table 1). Research studies in this field mainly refer to iron ore tailing (IOT). Pioneering investigations (Dutta et al., 1992; Dutta, Bordoloi, & Borthakur, 1997) indicate that the most suitable mix-design to be used for cold-bonded pellets containing IOT, must include cement/cement clinkers and other components. Indeed cold-bonded pellets produced with GGBS and Portland cement clinker in the ratio of 1:1, 2:3, and 3:2, had higher crushing strength compared to pellets containing larger amounts of clinker (Dutta et al., 1992). Similarly, cold-bonded pellets with suitable mechanical characteristics can be obtained adding silica fines (quartz silica or RHA) in the mixture. Moreover, it is reported that production of pellets with good characteristics can be possible also with lowered (from 10% to 4-6%) amount of binder (by enhancing the binder surface area to a value of about $4100 \text{ cm}^2 \text{ g}^{-1}$ (Dutta et al., 1997). As an alternative to calcium silicate cements (i.e. Portland cement), calcium aluminate cement, used at a similar level (7 wt%) also leads to the production of iron ore pellets with enhanced strength (Aota, Morin, Zhuang, & Clements, 2006).

Other inorganic binders used for the production of cold-bonded pellets containing IOT, are bentonite and $\text{Ca}(\text{OH})_2$. Bentonite dosed at about 0.5%, gave positive results especially for high Blaine numbers (fineness level) of hematite iron ore pellets (Pal, Ghorai, Agarwal, et al., 2015). $\text{Ca}(\text{OH})_2$ dosed between 10% and 14% (w/w) produced very high compressive strengths for siliceous IOT (McDonald, Roache, & Kawatra, 2016).

Organic binders such as molasses, have been used and added to the mixtures in percentages ranging between 20% and 50% (Cevik, Ahlatci, & Sun, 2013). This produced high compressive strengths in cold-bonded pellets, but at high dosages, it has an adverse effect on pellets porosity. A positive effect on pellets strength due to molasses addition can also be obtained coupling molasses with calcined lime (added, respectively in percentages of 4 wt% and 10 wt%), as reported by Pal, Ghorai, & Das (2015). In particular, they tested these mixtures for the production of cold-bonded pellets of IOT containing high amount of coal (38 wt%).

Good performances are reported in case of mixture design including slaked lime coupled with dextrose. The cold-bonded pellets produced are characterized by increasing compressive strength, as the amount in the mixture increases up to 10% (Sah & Dutta, 2010).

Finally, very high compressive strength were obtained for IOT cold-bonded pellets containing dextrin in a range between 1 and 5% (Agrawal et al., 2000). However, carboxymethyl-cellulose, dosed between 1-2%, produced a better performance than dextrin, even if this latter is coupled with bentonite, or substituted by calcium-lignosulfonate (Nikai & Garbers-Craig, 2016).

The cold-bonding process has been tested also on pyrrhotite and gold mill tailings (Amaratunga, 1995; Amaratunga & Hmidi, 1997). For both wastes several mixtures have been tested, with various composition of Portland cement and gypsum β -hemihydrate, added at different percentages. The results indicate that, to achieve a suitable compromise between reduced Portland cement consumption and high pellets strength, the best solution has 10% binder dosage, containing gypsum β -hemihydrate and Portland cement in a ratio of 40:60 for pyrrhotite

tailings (Amaratunga, 1995). In the case of gold mill tailings, the best result was observed for 4% binder dosage, containing gypsum β -hemihydrate and Portland cement in a ratio of 20:80 (Amaratunga & Hmidi, 1997).

3.3 Mix-design for pellets with different waste materials

Although FA are more frequently used for the production of cold-bonded pellets, BA is also used (Table 1). This can positively affect the characteristics of the final LWA, especially in terms of crushing resistance (Tang, Florea, & Brouwers, 2017). Both cement and lime can be used as binders to produce cold-bonded pellets containing BA. However the use of cement produces higher aggregate strength (Geetha & Ramamurthy, 2010a). To improve the pellets strength, is also possible to use chemical activation of the binder through Na_2SO_4 addition, which accelerates early pozzolanic activity (Geetha & Ramamurthy, 2010a). The addition of $\text{Ca}(\text{OH})_2$ to the mixtures increases pelletization efficiency and reduces pelletization times. In terms of pelletization efficiency, higher values correspond to binder percentages ranging around 14% for cement, lime and high swelling bentonite. Different values of binder percentages are reported around 25% for medium swelling bentonite and around 30% for clay (with plasticity index of 78 and 108), kaolin, and metakaolin (Geetha & Ramamurthy, 2010b).

$\text{Ca}(\text{OH})_2$ and Na_2SO_4 have also been used as pelletization and strength enhancing admixtures for cold-bonding of lignite and bituminous pond ash (Vasugi & Ramamurthy, 2014). For the pond ash overall properties were enhanced by increasing $\text{Ca}(\text{OH})_2$ and Na_2SO_4 content, especially when the used binder is cement instead of lime. In the case of lignite pond ash, the characteristics of cold-bonded pellets improved with increasing $\text{Ca}(\text{OH})_2$ and increasing hardening admixture (80% cement, 9% $\text{Al}_2(\text{SO}_4)_3$, 6% Na_2CO_3 and 5% CaO) dosage (Vasugi & Ramamurthy, 2014). Better results are obtained for both the pelletization efficiency and the

mechanical characteristics of the produced pellets, including the bulk density, the water absorption capacity, the open porosity and the mechanical strength.

Referring to other waste typologies (Table 1), it has to be mentioned the production of cold-bonded pellets composed by 35% basic oxygen furnace coarse sludge, 20% basic oxygen fine sludge, 20% blast furnace dust, 10% briquette fines, 5% filter dust, and 10% of Portland cement, tested by Robinson (2005). In addition, it has to be considered either the production of cold-bonded pellets containing iron oxides, produced using blast furnace slag (6%) and clinker (4%) as binders (Çamci, Aydin, & Arslan, 2002), and the use of various wastes as binders for quarry fines pellets production (Gunning, Hills, & Carey, 2009). For these latter, the quarry fines+waste mixtures are treated through accelerated carbonation during the pelletization phase. This approach allows the production of aggregates characterized by final physical and mechanical properties, which are comparable or even better than the corresponding characteristics of lightweight expanded clay aggregate.

The cold-bonding process has also been used to treat electric arc furnace dust (EAF), car fluff and fluxed hematite concentrate (Colangelo, Messina, Di Palma, & Cioffi, 2017; Mantovani & Takano, 2000; Zhou, Wattanaphan, & Kawatra, 2017). The addition of 3 or 5 wt% of Portland cement as binder produced good results in terms of cold compressive strength of pellets containing EAF and coal fine mixtures (Mantovani & Takano, 2000). Further tests focused on the determination of compressive strength after heating of EAF+coal fine pellets containing 5 wt% Portland cement and this indicated the need to reduce pellet size (max diameter=7 mm) to obtain high strengths (Mantovani, Takano, & Büchler, 2002). Colangelo et al. (2017) suggest the possibility of using up to 43.5% of car fluff to produce cold-bonded pellets.

It can be observed that higher crushing strength and reduced water absorption capacity result from decreasing the water to binder ratio, when coal FA and cement are used as binders. Finally, the study by Zhou et al. (2017) indicates that it is possible to produce cold-bonded pellets

containing fluxed hematite concentrate, using humic acid as the binder. In this case, results display good characteristics of the produced aggregate when the binder dosage is around 0.6 wt%.

4. Parameters affecting the cold-bonding process efficiency

The use of various waste types and mix-designs leads to different results in terms of aggregate quality and properties. However, cold-bonding process efficiency is also dependent on operational parameters (Table 2). The three parameters which mainly affect the pellets characteristics are the inclination angle and rotation speed of the pelletizer, which have the most important effect on the mechanical strength, and the moisture content of the mix which, influences of the pellet size (Harikrishnan & Ramamurthy, 2006).

Generally, increasing the inclination angle and the rotation speed of the pelletizer, or increasing the rotation speed and the duration length of the process improves the ten percent fine values due to the reduction of the pellets porosity (Manikandan & Ramamurthy, 2009).

However, the operational parameters have different effects on the pelletization efficiency depending on the pellets size (Table 2). Tests on cold-bonding pelletization of FA with high swelling bentonite indicate that increasing the rotation speed, the inclination angle, the process duration, the moisture content and the bentonite percentage results in beneficial effects for granules in the size range of 20-12.5 mm and 12.5-10 mm (Manikandan & Ramamurthy, 2009). For pellets size ranging from 4.75 to 10 mm, the best process efficiency is obtained by decreasing the rotation speed and the pelletizer inclination angle, or decreasing the process duration length and increasing the bentonite content.

The effect of the rotation speed and the inclination angle seems to be less on final pellets characteristics when mixes contain a high percentage of cement (Tajra et al., 2018). Similarly, a reduced effect of these two parameters compared to the others (i.e. moisture and binder

contents, and process duration) is observed for pellets with fineness of $257 \text{ m}^2 \text{ kg}^{-1}$ and in the case of use of bentonite or kaolinite as binders (Manikandan & Ramamurthy, 2007). This effect becomes more important, for pellets with fineness of $414 \text{ m}^2 \text{ kg}^{-1}$, prepared without binder addition. Moreover, a good pelletization efficiency can be observed up to certain rotation speed limit because higher values lead to the prevalence of centrifugal force on gravitational ones with consequent particles adhesion on pelletizer sides and lowered process efficiency (Colangelo & Cioffi, 2013).

The typology of the aggregate and the curing method are essential in determining final pellets properties. Accelerated curing methods such as autoclaving or steam curing do not lead to production of pellets with improved properties compared to those obtained following a normal water cured method (Manikandan & Ramamurthy, 2008). Fig. 2 provides an example of qualitative variation trends for the aggregates mechanical performance at different values of the operating parameters.

5. Application of the cold-bonded pellets

The main practical applications of LWAs are reviewed in the following subsections. The feasible LWAs reuse for manufacturing of products characterized by suitable properties is strongly dependent on several operating conditions. Table 3 summarizes the main LWAs applications, operating conditions and their consequent effects on the product properties. Moreover, illustrative representation of qualitative variation trends for mechanical performance of concretes made by artificial aggregates is reported in Fig. 2 as a function of the operating parameter values increase.

5.1 Cold-bonded pellets as aggregates for lightweight concrete

Cold-bonded pellets are frequently employed as aggregates for the production of lightweight concrete (LWC). This application provides the possibility of massive waste reuse in concrete production, especially when LWC is prepared using FA both as a cementitious material and as cold-bonded aggregate (Rivera et al., 2015).

The partial replacement of natural aggregates by cold-bonded LWA in LWC results in a concrete characterized by suitable properties for classical applications of the final product. For instance, the use of FA pellets as LWC aggregates gives rise to good results in terms of compressive and split-tensile strength, static elastic modulus and shrinkage behavior, although high volume ratios of added pellets cause an overall worsening of these properties (Gesoglu, Özturan, & Güneyisi, 2004). Indeed, above certain values of the cement content, the volume fraction aggregate increase can lead to reduced concrete strength, due to the change of predominant failure mode to aggregate fracture (G. Joseph & Ramamurthy, 2009b). The best results in terms of concrete compressive strength enhancement are usually observed for LWC using cold-bonded FA pellets to replace the sand, (G. Joseph & Ramamurthy, 2009a). However, despite the observable LWC properties enhancement achieved with high sand substitution rates, literature results indicate that normal weight concrete presents better characteristics compared to light weight one containing FA pelletized aggregates (Kockal & Ozturan, 2011b; Patel, Patil, Patil, & Vesmawala, 2018).

Negative effects on the compressive strength value of the final product can be obtained by increasing the FA pellets replacement level in LWC that are subjected to water or steam curing (Gesoglu, Güneyisi, Ali, & Mermerdaş, 2013). Steam curing allows a total replacement of natural aggregates with FA cold-bonded pellets and the possibility of using the final product as structural concrete within 24 h. Steam curing is generally preferred to hot water curing to enhance LWC properties. Such a result can be observed at various replacement level (40, 50 and 62%) of cold-bonded aggregates made by FA+bentonite mixture after 3, 7, and 28 d of

curing (Gomathi & Sivakumar, 2015). Similarly, LWC specimens subjected to oven curing at 200 °C present better mechanical properties than specimens subjected to water curing (Vijay & Singh, 2014). Nonetheless, experiments testing various curing methods (i.e. mist-cured, air-cured, and sealed) on LWC made by FA aggregates do not indicate significant differences in terms of compressive strength and degree of hydration. This latter result can be ascribed to the autogenous curing in the cold-bonded aggregates (G. Joseph & Ramamurthy, 2011).

LWC properties strongly depend on the characteristics of the adopted cold-bonded pellets. For example, comparing LWC concrete made by FA and LWC concrete made by quarry dust aggregates, it is showed a higher compressive strength of the former, and better values of the compacting factor and porosity for the latter (Harilal & Thomas, 2013). According to the study of Thomas & Harilal (2015) a higher compressive strength can be obtained for LWC made by quarry dust+FA aggregates, increasing the amount of FA. However, heating tests aimed at determining the LWC residual compressive strength, indicate the suitable applicability of quarry dust alone for concrete manufacture. In fact, satisfactory results on the compressive strength are reported up to 400 °C for the quarry dust-LWC, compared to the maximum value of 300 °C obtained in case of FA-LWC (N. Joseph, Harilal, Paul, & Thomas, 2013; Thomas & Harilal, 2016). A further example is provided by the study of Gesoğlu, Özturan, & Güneyisi (2006) examining the effect of four different aggregates addition (45% of concrete volume) on LWC. This study shows that the use of 20% cement and 80% FA was the best solution in terms of mechanical strength of the final product.

A possible enhancement of LWC properties can be obtained using LWAs containing mechanically activated FA, which result in an improvement of compressive strength and a substantial reduction in porosity and shrinkage of the concrete (Terzić et al., 2015). Another possibility is the use of silica fume and/or steel fibers in the concrete preparation (Güneyisi, Gesoğlu, & Ipek, 2013; Güneyisi, Gesoğlu, Pürsünlü, & Mermerdaş, 2013). Good results are

obtained preparing FA-LWC with the addition of silica fume at 10%, steel fibers at 0.75%, and using a water to binder ratio of 0.35 (Gesoğlu, Güneyisi, Alzebaree, & Mermerdaş, 2013). In general, the addition of steel fibers improves the splitting tensile and flexural strength as well as fracture energy and characteristic length (Güneyisi, Gesoglu, Özturan, & Ipek, 2015). Also, the involvement of FA geopolymer aggregates in concrete production can lead to improved mechanical properties compared to concrete made by addition of commercial lightweight expanded clay aggregates (LECA) (Yliniemi et al., 2017). Referring to concrete shrinkage, weight loss and age of cracking, positive effects are observed, by adding admixtures able to reduce the shrinkage effect (from 0.75% to 3% by cement weight) in the LWC preparation (Güneyisi et al., 2014). Good mechanical properties of the LWC are also obtained employing stoker furnace FA+cement pellets (70%+30%, respectively) which had a second-pelletization step, adding, as binder a cement:coal FA ratio equal to 1:1 (Colangelo et al., 2015).

It has to be finally observed that, although LWC produced using cold-bonded FA aggregates has reduced mechanical properties compared to the equivalent LWC produced using sintered FA aggregates (Kockal & Ozturan, 2010, 2011a), some exceptions exist. Chang & Shieh (1996) report that LWC made by cold-bonded FA aggregates has a higher compressive strength (33.9 MPa) compared to LWC made with sintered LWA (30.1 MPa) after 28 days curing. Frankovič et al. (2017) indicate that granulated FA aggregate addition to LWC results in lower compressive and tensile strength compared to LWC made from crushed FA aggregates or crushed natural limestone aggregates even after 90 days curing.

5.2 Cold-bonded pellets as aggregates for self-compacting concrete

Cold-bonded aggregates can also be used for the production of self-compacting concrete (SCC). Experiments aimed at investigating the effect of different replacement level of natural coarse aggregates with cold-bonded aggregates mainly prepared from GGBS, show the possibility of

producing a stable material, even when the replacement is complete (i.e. 100%) (Gesoglu, Güneyisi, Mahmood, öz, & Mermerdaş, 2012). Generally, different replacement levels of coarse and/or fine FA-LWA, produce a SCC characterized by suitable deformability, passing ability, and segregation resistance (Gesoglu, Güneyisi, Özturan, Öz, & Asaad, 2014b). Moreover, increasing the FA-LWA replacement level can entail the decrease of SCC density and plastic viscosity as well as a lower high-range-water-reducing-admixture amount required for a specific concrete workability (Gesoglu, Güneyisi, Ozturan, Oz, & Asaad, 2015). Despite this, the increasing replacement level of FA-LWA instead of natural aggregate in SCC can cause lower splitting and compressive strength values due to the weakness of cold-bonded aggregates (Gesoglu, Güneyisi, Özturan, Öz, & Asaad, 2014a). Compared to control tests (only Portland cement as binder), SCC made by FA-LWA as aggregates results in a decreased slump flow and V-funnel flow times and increased L-box height ration. This latter result is achievable with combined use of FA and silica fumes in ternary blends with Portland cement (Güneyisi, Gesoglu, & Booya, 2012). The use of ternary blends with Portland cement, FA and silica fumes for SCC preparation can lead to an improvement in the compressive strength achieving comparable values of binary blends with Portland cement and FA or only Portland cement (Güneyisi, Gesoglu, Booya, & Mermerdaş, 2015). The concurring use of SiO₂ nanoparticles and cold-bonded FA-LWA treated by soluble sodium silicate solution appears to be very interesting for SCC production (Güneyisi, Gesoglu, Azez, & Öz, 2015, 2016). Improved concrete performance and reduced drying shrinkage compared to the untreated FA aggregates produced with an optimal blend made from 5% of SiO₂ nanoparticles and treated FA aggregates. Nonetheless, the use of these components may cause a significant decrease in the SCC permeability, as reported by Güneyisi, Gesoglu, Azez, et al. (2015). Further treatment of cold-bonded aggregates can be effective to produce a material suitable for the production of SCC. For instance, Hwang & Tran (2015) propose the use of H₂O₂ as foaming

agent for the production of LWA aggregate made by FA+GGBS. According to their results, the adoption of foamed LWA aggregates can be useful to obtain SCC characterized by suitable properties.

FA cold-bonded aggregates have good characteristic as self-curing agent. In fact, the water absorbed by the aggregates during their pelletization can be gradually released to the cement particles in the concrete allowing further hydration process and concrete characteristics improvement. Coupled with LECA, FA-LWA leads to SCC production with very high compressive strength, split tensile strength and flexural strength under self-curing conditions. According to the study, the reported results were achieved with replacement levels of 5% of LECA and 30% of FA-LWA (Gopi, Revathi, & Kanagaraj, 2015). SCC characterized by good mechanical properties can be also obtained under water-curing conditions, with replacement levels of 5% of LECA and 40% of FA-LWA (Gopi et al., 2015). Tests investigating the characteristics of SCCs made by combining waste LWA (MSWI BA, PSA, coal FA, and washing aggregate sludge) with or without addition of materials for aggregates property enhancement (i.e. nano-silica and polypropylene fiber) (Tang & Brouwers, 2018) showed a decrease of SCC flexural and compressive strength for all the concrete mixtures compared to the control conditions. This result is more noticeable for the concrete obtained using the lowest replacement level (30%). It was observed that the slump flow diameter decreased only for SCC made by combined waste LWA+polypropylene fiber, and an overall V-funnel time increased compared to the control condition for all the tested concretes having the highest aggregate replacement level (60%) (Tang & Brouwers, 2018).

5.3 Cold-bonded pellets for less investigated applications

The use of pelletized aggregates for self-compacting mortars (SCM) is not frequently reported in the scientific literature. Nonetheless, the use of FA-LWA as replacement material in SCM

shows promising applicability. The increase of the FA-LWA replacement level leads to the improvement of SCM properties such as workability and flowability, although it negatively affects the SCMs strength and porosity (Güneyisi, Gesoğlu, Altan, & Öz, 2015). Other effects of increasing FA-LWA replacement level values on SCM, are reported by Güneyisi, Gesoglu, Ghanim, Ipek, & Taha (2016). These authors indicate an increase of the SCM V-funnel flow time, associated to a decrease of the slump flow diameter, with increasing percentage of added FA-LWA. Both effects are significantly affected by the water-to-binder ratio (w/b) with the lowest variations observed for the highest tested ratio (0.44). At the same time, the highest SMC compressive strength is obtained increasing the FA-LWA replacement level, while keeping the lowest w/b ratio (0.33) (Güneyisi, Gesoglu, Ghanim, et al., 2016).

Negative effects on mortars compressive strength are observed on increasing the replacement level of cold-bonded bottom-ash LWA. Obtained values are lower compared to the compressive strength of mortars produced with raw bottom-ash or expanded shale aggregates, using the same replacement percentage (Kim, Ha, & Lee, 2016). At the same time, the use of cold-bonded bottom-ash aggregates allows higher reductions of the mortar autogenous-shrinkage, due to the higher water absorption of the cold-bonded aggregate samples.

Few studies have investigated the applicability of cold-bonded pellets as adsorbent, for metal removal from aqueous solutions. Tests on arsenic ions sorption using cold-bonded FA indicate that the process can achieve good removal efficiencies (Polowczyk et al., 2007). Process kinetics follow a Lagergren pseudo-first-order model which has a similar form as the Boyd film diffusion model. According to Polowczyk et al. (2007), this latter aspect makes it unclear if the process is controlled by a pseudo-first order reaction or diffusion. Suitable adsorption capacity of cold-bonded FA is reported also for copper and cadmium (Papandreou, Stournaras, & Panias, 2007). The process appears to be reversible in acidic condition (Papandreou et al., 2007), strengthening the significance of the potential application of cold-bonded pellets to replace

natural aggregates in cement matrixes. This clearly highlights the opportunity to reduce contaminants leaching phenomena, and ensure environmental sustainability.

6. Conclusions

The literature overview reported in the present work highlights the significant applicability of the cold-bonding process as a sustainable solution for the disposal of several waste types. In this perspective, the cold-bonding process displays i) interesting waste treatment results in the production of stabilized aggregates; and ii) wide applicability of the produced cold-bonded aggregates in the construction sectors. Therefore, the process answers to the modern world requirements of more environmentally sustainable practices for waste disposal, and can be fully ascribed in the framework of new technologies inspired by the principle of the circular economy. The environmental-friendly and cost-saving characteristics of the cold-bonded process compared to sintering represent a further advantage which emphasizes the scientific and practical interest. However, according to the literature, the methodology aimed at producing cold-bonded aggregates characterized by proper characteristics usable for concretes can be affected by different factors. The latter are mainly represented by i) the different characteristics of the waste used for aggregates production; ii) the component proportions adopted for the aggregate mix-design; iii) the selection of the operating parameters; iv) the aggregates replacement level in the concrete mixture; and v) the environmental factors affecting the aggregate characteristics. Providing a wide overview of different experimental studies on the cold-bonding process, the present work allows the main process advantages/disadvantages to be identified. The detailed information reported can be useful to further support practical decision-making focused on the selection of suitable operating conditions for a high efficient cold-bonded process producing aggregates with usable properties.

533 **Acknowledgements**

534 Dr. Ferraro would like to thank the Italian Ministry of Education, University and Research
535 (MIUR) which provided financial support for 12 months post-doctoral grant in the framework
536 of the research project entitled “Dipartimenti di Eccellenza” per Ingegneria Civile, Edile e
537 Ambientale – CUP E65D18000820006.

Table 1. Effects of relevant mix-designs on the cold-bonding pellets characteristics.

Pellet mix-design	Main result	Reference
Waste material: ore mix (from 88 to 90%) Binder: clinker (used alone or in different ratio with granulated blast furnace slag), granulated blast furnace slag (used in different ration with clinker) Addition: gypsum (used at 3% in 1:1=granulated blast furnace slag:clinker binder at 12%)	• Higher crushing strength observed for steam cured pellets compared the normal and accelerated cured ones • Higher porosity after 28 d of normal curing conditions • Highest crushing strength after 28 d of normal curing for mixture with ore mix+clinker (88%:12%)	Dutta et al. (1992)
Waste material: pyrrhotite tailings mixed with binder percentage values of 2, 4, 6, 8, and 10% Binder: cement+gypsum β -hemihydrate (used in percentage variable from 100 to 0%)	• Increasing fracture load (N pellet⁻¹) with increasing pellet diameter • Highest fracture load (over the whole curing period ranging from 0 to 28 d) for pellets with 100% of cement and binder dosage of 10% • Optimal binder mixture observed for pellets with binder cement+gypsum β-hemihydrate of 40%:60%	Amaratunga (1995)
Waste material: gold mill tailings mixed with binder percentage values of 2, 4, 6, 8, and 10% Binder: cement+gypsum β -hemihydrate (used in percentage variable from 100 to 0%)	• Increasing fracture load (N pellet⁻¹) with increasing pellet diameter for all the curing period values (1, 3, 7,14, and 28 d) • Pellet optimal conditions with binder dosage of 4% and binder cement+gypsum β-hemihydrate of 80%:20% for pellets diameters equal to 12.7 and 19 mm • Fulfilling fracture load strength (237 N pellet⁻¹) and lowest Portland cement consumption percentage (3.2%) after 3 d of curing with binder dosage of 4% and binder cement+gypsum β-hemihydrate of 80%:20% for pellets diameter equal to 19 mm	Amaratunga & Hmidi (1997)
Waste material: blue dust (90-96%) Binder: cement (4-10%) Addition: water (5-9% on dry raw mixture basis) and partial replacement of binders with rice husk ash silica or quartz silica (0.4-0.8%) for some mixture	• Higher early crushing strength values (at 1 d) observed by partially replacing cement with silica fines • Overall higher crushing strength values for accelerated cured pellets compared to normal cured ones	Dutta et al. (1997)
Waste material: iron ore (from 95 to 85%) mixed with coal (from 5 to 15%) or activated char (10%) or petroleum coke (10%) Binder: oil slush (5%), sodium silicate (5%), bentonite (6%), molasses (9%), slake lime (7%), and dextrin (from 1 to 5%)	• Higher similar values of dry strength for mixture with binder mixtures+iron ore:coal (90%:10%)+dextrin (30 kg pellet⁻¹ for 4% of dextrin and 31 kg pellet⁻¹ for 5% of dextrin) • Lower similar decrepitation values • Highest reduced pellets strength observed for sample with 4% of dextrin as binder, granulometry of 40%, and internal reductant percentage of 10% (using non-coking coal as reductant)	Agrawal et al. (2000)
Waste material: fly-ash (100 or 92%) Binder: cement (8%) or lime (8%)	• Highest crushing values for pellets whit cement at 7 and 14 curing days • Highest crushing strength at 28 curing day for pellets whit lime	Baykal & Döven (2000)

Waste material: electric arc furnace dust with specific surface area of $4.32 \pm 0.21 \text{ m}^2 \text{ g}^{-1}$ (82.7%) and $0.59 \pm 0.04 \text{ m}^2 \text{ g}^{-1}$ (80.9%) Binder: cement (used at 3 and 5%), coal (used at 19.1 and 17.3%) Addition: CaCO_3 (used at 12%)	• Cold compressive strength improvement with addition of 3 and 5 wt% of cement • No decrepitation occurrence after test at 700 °C for dried pellets with 3 and 5 wt% of cement • Zn removal enhancement (1124 °C) from pellets by adding 5 wt% of cement or 12 wt% of CaCO_3	Mantovani & Takano (2000)
Waste material: coarse mill scale (40%), blast furnace sludge (20%), blast furnace dust (15%), basic oxygen furnace sludge (15%), basic oxygen furnace dust (5%), and oily mill scale (5%) Binder: blast furnace slag (6%) and clinker (4%) Addition: coke (from 5 to 20%) or graphite (from 4.1 to 16.5%)	• Best reduction degree with coke as reducing agent compared to the graphite • Reduction degree increase with increasing $C_{\text{fix}}/\text{Fe}_{\text{total}}$ ratio • Increase of the reduction period with decreasing temperatures	Çamci et al. (2002)
Waste material: electric arc furnace dust with specific surface area of $3.62 \pm 0.41 \text{ m}^2 \text{ g}^{-1}$ (83.3%) and $4.32 \pm 0.21 \text{ m}^2 \text{ g}^{-1}$ (82.7%) Binder: cement (used at 5%), coal (used at 16.7 and 17.3%) Addition: CaCO_3 (used at 12%) or KCl (used at 12%)	• Significant compressive strength decrease after heating treatment for mixtures with electric arc furnace dust+coal (83.3%:16.7%) and electric arc furnace dust+coal+cement (83.3%:16.7%:5%) at pellets size of 14 mm • No compressive strength decrease after heating treatment for mixture with electric arc furnace dust+coal+cement (83.3%:16.7%:5%) at pellets size of 7 mm • Best Zn removal for mixture with electric arc furnace dust+coal+KCl (82.7%:17.3%:12%) at 1123.85 °C • No significant differences with various additives at about 1199.85 °C or higher temperatures	Mantovani et al. (2002)
Waste material: fly-ash (from 90 to 80%) Binder: cement (from 10 to 20%)	• Specific gravity increase (from 1.65 to 1.76) and water absorption decrease (from 34.4 to 20.8%) with increasing cement percentage from 10 to 20% • Increase of bulk unit weight (from 857 to 972 kg m^{-3}) and particle strength (from 6.01 to 8.57 MPa) with increasing cement percentage from 10 to 20%	Chi et al. (2003)
Waste material: basic oxygen furnace coarse sludge (35%), basic oxygen furnace fine sludge (20%), blast furnace flu dust (20%), briquette fines (10%), and filter dust (5%) Binder: cement (10%)	• Fe_2O_3 reduction to Fe_3O_4 between 500 and 600 °C • Fe_3O_4 reduction to FeO between 640 and 850 °C • FeO reduction to Fe between 850 and 1200 °C • Carbonate decomposition occurrence at about 700 °C forming $\text{Ca}_2\text{Fe}_2\text{O}_5$ and other products	Robinson (2005)
Waste material: iron ore (91.5%) Binder: alumina cement (7%), bentonite (0.6%)+0.9% silica fume+0.14 super plasticiser Addition: silica fume (0.9%), super plasticiser (0.14%)	• Average point strength of pellets with alumina cement equal to 2300 N • Higher crushing strength values for pellets with alumina cement compared to pellets made by Portland cement	Aota et al. (2006)

Waste material: fly-ash (100% or 90-70%) Binder: cement (from 10 to 30%)	- Increasing shear strength with increasing cement percentage addition - Specific gravity increase and water absorption decrease of the aggregates with increasing cement content	Arslan & Baykal (2006)
Waste material: fly-ash type A, fly-ash type B, fly-ash type A with water glass surface treatment Binder: cement	- Highest crushing strength for pellets with B type fly-ash - Highest water absorption values for type A fly-ash - Lowest water absorption values for pellets with A type surface treated fly-ash	Gesoğlu et al. (2007)
Waste material: fly-ash class F Binder: bentonite (from 4 to 14%) or kaolinite (from 4 to 30%)	- Pelletization efficiency increase from 48 to 98% with increasing content of bentonite - Pelletization efficiency increase from 29 to 98% with increasing content of kaolinite	Manikandan & Ramamurthy (2007)
Waste material: quarry fines Binder: biomass ash, cement bypass, kiln dusts, MSWI bottom ash and fly-ash, paper ashes, pulverized fuel ash, sewage sludge ash, and wood ash (used as CO ₂ -reactive binders with addition from 10 to 50%)	Similar properties for all the carbonated LWAs compared to commercially available LWAs	Gunning et al. (2009)
Waste material: fly-ash class F (fineness of 257 m ² kg ⁻¹) Binder: high swelling bentonite (from 6 to 14%) or medium swelling bentonite (from 9 to 21%)	- Pelletization efficiency equal to 98% with 14% of high swelling bentonite - Pelletization efficiency equal to 97% with 21% of medium swelling bentonite	Manikandan & Ramamurthy (2009)
Waste material: bottom ash Binder: cement or lime Addition: Ca(OH) ₂ (as pelletization admixture) or Na ₂ SO ₄ (as chemical activator)	- Optimal mixture values (expressed as % by weight of BA) equal to 31.27% (moisture content), 1.59% (Ca(OH)₂), 8.99% (binder), 3.19% (Na₂SO₄) for cement - Optimal mixture values (expressed as % by weight of BA) equal to 31.19% (moisture content), 1.47% (Ca(OH)₂), 8.99% (binder), 3.19% (Na₂SO₄) for lime - Values equal to 92.8% of pelletization efficiency, 928.6 kg m⁻³ of bulk density, 2.41 t of ten percentile fines, 35.1% of porosity, 19.1% of water absorption with optimal mixture of cement - Values equal to 90.7% of pelletization efficiency, 920.8 kg m⁻³ of bulk density, 2.18 t of ten percentile fines, 36.8% of porosity, 19.3% of water absorption with optimal mixture of lime	Geetha & Ramamurthy (2010a)
Waste material: bottom ash Binder: cement or lime (as cementitious binders from 0 to 14%) and kaolin, metakaolin, clay with plasticity index of 78 and 108, medium swelling bentonite, or high swelling bentonite (as clay binders from 0 to 30%) Addition: Ca(OH) ₂	- Maximum pelletization efficiency (97-98%) without Ca(OH)₂ addition with high swelling bentonite (14%), medium swelling bentonite (25%), other clay binders (30%), cement and lime (14%) - Pelletization efficiency improvement 97-98% with Ca(OH)₂, 10 % with high swelling bentonite, cement and lime, 18% with medium swelling bentonite, 20% with kaolin, metakaolin and clay with plasticity index of 78, 25% with clay with plasticity index of 108	Geetha & Ramamurthy (2010b)

Waste material: iron ore (from 58.70 to 69.28%), coal from mines (32.49 to 23.12%) and from steel plant (from 28.99 to 20.33%) Binder: 10% of slaked lime and 5% of dextrose on iron ore weight basis (used from 8.81 to 10.39%)	- Highest compressive strength equal to 330 ± 10.31 N pellet⁻¹ for mixture with iron ore+mines coal+binder (66.85%:23.12%:10.03%) and 362 ± 11.72 N pellet⁻¹ for mixture with iron ore+steel plant coal+binder (69.28%:20.33%:10.39%) - Minimum shatter index equal to 0.336% for mixture with iron ore+mines coal+binder and 0.245% for mixture with iron ore+steel plant coal+binder	Sah & Dutta (2010)
Waste material: fly-ash (added in binary and ternary mixture from 90 to 30%) Binder: cement (added in binary and ternary mixture from 10 to 30%) Addition: granulated blast furnace slag (added in ternary mixture from 15 to 45%) or rice husk ash (added in ternary mixture from 15 to 45%)	- Better results in terms of aggregate compressive strength with addition of granulated blast furnace slag compared to rice husk ash addition - Water absorption increase and aggregate unit weight decrease with increasing addition of rice husk ash - Opposite tendency by increasing the addition of granulated blast furnace slag	Bui, Hwang, Chen, & Hsieh (2012)
Waste material: fly-ash (alone or added in binary and ternary mixture from 75 to 50%) Alkaline activator: 10M NaOH+sodium silicate Addition: granulated blast furnace slag (added in binary or ternary mixture from 13 to 50%) and rice husk ash (added to binary or ternary mixture from 12 to 50%)	- Higher crushing strength for fly-ash+granulated blast furnace slag aggregates (about 15 MPa) - Highest absorption capacity (20.5%) for fly-ash+rice husk ash (50%:50%) aggregates - Lowest value absorption capacity (7.8%) for fly+granulated blast furnace slag (50%:50%) aggregates	Bui, Hwang, Chen, Lin, et al. (2012)
Waste material: hematite (from 78.12 to 83.17%), coke (from 18.16 to 13.87%), and limestone (from 3.71 to 3.31%) Binder: molasses (from 20 to 50%)	- Higher compressive strength and lower porosity values with 50% of molasses for each Fe_{tot}/C_{fix} ratio - More similar compressive strength and porosity values for 50% and 40% of molasses in mixture with hematite:coke:limestone=83.17%:13.87%:3.31% (Fe_{tot}/C_{fix} ratio=3.5)	Cevik et al. (2013)
Waste material: weathered fly-ash (added in binary, ternary and quaternary mixture from 90 to 20%) Binder: lime (added in binary, ternary and quaternary mixture from 10 to 30%) Addition: wastewater treatment sludge (added in ternary and quaternary mixture from 50 to 60%) and desulfurization device sludge (added in ternary and quaternary mixture from 30 to 10%)	- Highest strength values for fly-ash+lime (60%:40%) and fly-ash+lime+desulfurization device sludge (40%:30%:30) aggregates - Lowest strength values for fly-ash+lime+wastewater treatment sludge (30%:20%:50 and 24%:16%:60) - Lower density values for ternary mixture with 30% desulfurization device sludge and both quaternary mixture aggregates	Ferone et al. (2013)
Waste material: fly-ash class F (used alone or binary mixture at 80 or 70%) Binder: cement (20%), furnace slag (30%), metakaolin (30%) or bentonite (20%) Addition: NaOH in all the mixtures	- Highest crushing strength for mixture with fly-ash+furnace slag (70%:30%) at all sizes (values from 22.81 to 12.80 MPa with decreasing pellets size) - Highest efficiency (99.07%) for mixture with furnace slag aggregates - Lowest efficiency (66.95%) for mix with on fly-ash	Gomathi & Sivakumar (2014)

Waste material: bituminous pond ash or lignite pond ash Binder: cement (for both wastes) or lime (for bituminous pond ash) Addition: Na₂SO₄ (for bituminous pond ash), Ca(OH)₂ (for both wastes), and hardening admixture (i.e. carbonic aluminate salt made by 80% of cement, 9% of Al₂(SO₄)₃, 6% of Na₂CO₃, and 5% of CaO) for lignite pond ash	• Maximum pelletization efficiency of bituminous pond ash-cement mixture equal to 78% with Ca(OH)₂ and 20% of binder • Maximum pelletization efficiency of bituminous pond ash-cement mixture equal to 98% without Ca(OH)₂ and 20% of binder • Maximum pelletization efficiency of bituminous pond ash-lime mixture equal to 79 with Ca(OH)₂ and 20% of binder • Maximum pelletization efficiency of bituminous pond ash-lime mixture equal to 96% without Ca(OH)₂ and 20% of binder • Maximum pelletization efficiency of lignite pond ash-cement mixture equal to 82 with Ca(OH)₂ and 20% of binder • Maximum pelletization efficiency of lignite pond ash-cement mixture equal to 99% without Ca(OH)₂ and 20% of binder • Bulk density and ten percent fines value increase with increasing dosage of binder+Na₂SO₄ and Ca(OH)₂ addition for bituminous pond ash • Water absorption and porosity decrease with increasing dosage of binder+ Na₂SO₄ and Ca(OH)₂ addition for bituminous pond ash • Bulk density and ten percent fines value increase with increasing dosage of hardening admixture and Ca(OH)₂ for lignite pond ash • Water absorption and porosity decrease with increasing dosage of hardening admixture and Ca(OH)₂ for lignite pond ash	Vasugi & Ramamurthy (2014)
Waste material: rotary furnace fly-ash (used in binary and ternary mixture from 70 to 50%), stoker furnace fly-ash (used in binary and ternary mixture from 70 to 50%) Binder: cement (used in binary mixture at 30%), lime (used in binary and ternary mixture at 30 and 15%), coal fly-ash (used in ternary mixture at 25 and 20%) Double-step pelletization: 1:1=cement:coal fly-ash binder mixture in amount equal to 40% of the granules weight	• Significantly high crushing strength values, low water absorption capacity and Los Angeles coefficient values for double-step pelletization mixtures with stoker furnace fly-ash+cement (70%:30%), stoker furnace fly-ash+lime+coal fly-ash (60%:15%:25%), and stoker furnace fly-ash+lime+coal fly-ash (50%:30%:20%) • Low heavy metals leaching for all the granules except for the granules produced with only lime as binder	Colangelo et al. (2015)
Waste material: fly-ash class F (80%) Binder: bentonite (20%) Addition: water (25% of binder weight) mixed with 10M NaOH	• Higher crushing strength of sintered aggregates of 10 mm (20.62 MPa) and 12 mm diameter (18.34 MPa) compared to cold-bonded ones at 10 mm (10.22 MPa) and 12 mm (14.51 MPa)	Gomathi & Sivakumar (2015)
Waste material: fly-ash (used in binary and ternary mixture from 80 and 70%) Binder: cement (used in ternary mixture at 10%), ground blast furnace slag (used in binary and ternary mixture at 20%) Addition: H₂O₂ (used in binary and ternary mixture from 3.5 to 8.75%) and surface treatment with alkaline solution 2.5M SiO₂/Na₂O (used in binary and ternary mixture at 5-7% aggregates by weight)	• Overall decreasing crushing and particle crushing strengths with increasing percentage of hydrogen peroxide for mixtures with and without cement addition; • Higher crushing and particle crushing strengths for aggregates with surface treatment compared to aggregates without surface treatment • Overall increasing water absorption with increasing percentage of H₂O₂	Hwang & Tran (2015)

Waste material: iron ore fines Binder: bentonite (from 0.4 to 0.8 wt %)	- Increasing dry compressive strength of green pellets with increasing bentonite percentage and increasing values of Blaine fineness - Increasing cold crushing strength values with increasing hardening temperatures and increasing Blaine fineness	Pal, Ghorai, Agarwal, et al. (2015)
Waste material: iron ore mixed with various percentage of carbon (from coal) Binder: molasses	- Higher decrease of cold compressive strength by increasing coal percentage from 0 to 20 wt% in pellets with 10 wt% of calcined lime and no molasses compared to pellets with 10 wt% of calcined lime and 3 wt% of molasses - Higher cold compressive strength for pellets with 3 wt% of molasses also with coal percentage value higher than 20 wt% - Increasing abrasion loss by increasing coal percentage from 0 to 20 wt% in pellets with 10 wt% of calcined lime and no molasses - Almost constant abrasion loss for pellets with 10 wt% of calcined lime and 3 wt% of molasses also with coal percentage higher than 20 wt%	Pal, Ghorai, & Das (2015)
Waste material: siliceous ore tailings Binder: $\text{Ca}(\text{OH})_2$ (from 6 to 14%)	- Highest compressive strength observed within 15 min for 14% of $\text{Ca}(\text{OH})_2$ - Highest pellet porosity (25%) observed for 12% of $\text{Ca}(\text{OH})_2$	McDonald et al. (2016)
Waste material: iron ore fines Binder: carboxymethyl-cellulose or calcium-lignosulfonate (used at 1 or 2%), dextrin or dextrin+bentonite (used at 3 or 4%) Addition: coke (used at 15 and 20%)	- Overall dry strength increase with increasing binder percentage (for all the binders) and decreasing coke percentage - Highest dry strength value by adding 4% of dextrin+bentonite - Optimal binder represented by the carboxymethyl-cellulose addition with dry strengths in excess of 300 N peller⁻¹, metallization value up to 95.5% (pellets reduction at 1100 °C for 20 min), and decrepitation indices lower than 0.1%	Nikai & Garbers-Craig (2016)
Waste material: peat wood fly-ash (used alone or in binary mixture at 80 and 60%) Binder: blast furnace slag (used in binary mixture at 20 and 40%), coal fly-ash (used in binary mixture at 20 and 40%), and metakaolin (used in binary mixture at 20 and 40%) Addition: H_2O or $\text{K}_2\text{O}_3\text{Si}$ as liquid binders	- Strongest granules with alkali activators and blast furnace slag - Lowest strength for the mixture with peat wood fly-ash+H_2O	Yliniemi, Nugteren, et al. (2016)
Waste material: fly-ash from electrostatic precipitator and silos of fluidized bed combustion treatment Addition: sodium silicate as alkali activator	- Best aggregate strength with highest amount of selectively soluble SiO_2 and Al_2O_3 - Leaching increase after alkali activation especially for anionic heavy metal species	Yliniemi, Pesonen, et al. (2016)
Waste material: fuel-biofuel fly-ash (used alone or in binary mixture at 80 and 60%) Binder: blast furnace slag (used in binary mixture at 20 and 40%) and metakaolin (used in binary mixture at 20 and 40%)	Highest crushing strength for mixture with fly-ash+blast furnace slag (60%:40%) for samples cured in plastic bags for 28 d or immersed in water for 3 d	Yliniemi, Tiainen, et al. (2016)

Waste material: car fluff (coal fly-ash:car fluff ratio equal to 0.83) Binder: cement+coal fly-ash (water to binder ratio equal to 0.41, 0.36, and 0.31)	• Highest crushing strength (5.2 ± 0.4 MPa) for lower water to binder ratio • Lowest water absorption ($10.3 \pm 0.7\%$) for lower water to binder ratio • Heavy metals immobilization degree higher than 90% for all the samples	Colangelo et al. (2017)
Waste material: fly-ash (used in multiple additions mixture at 100 and 50% on total fly-ash+paper sludge ash) Binder: cement (used in multiple additions mixture from 5 to 15% on total solids) Addition: bottom ash fines (used in multiple additions mixture from 10 to 75% on total solids), paper sludge ash (used multiple additions mixture at 50% on total fly-ash+paper sludge ash), washing aggregate sludge (used in multiple additions mixture at 5% on total solids), granulated blast furnace slag (used in multiple additions mixture at 67% on cement), and polypropylene fibre (used in multiple additions mixture from 1 to 4.5% on volume)	• Best crushing strength values (after 28 d curing) for mixture with cement+fly-ash+paper sludge ash+bottom ash fines+washing aggregate sludge (15%:50%:50%:40-75%:5% of the corresponding weight basis) and mixture with cement+fly-ash+paper sludge ash+bottom ash fines+washing aggregate sludge+polypropylene fibre (10%:50%:50%:40-75%:5%:2.5% of the corresponding weight and volume basis) • Lowest crushing strength values for mixture with cement+granulated blast furnace slag+fly-ash+paper sludge ash+bottom ash fines+washing aggregate sludge (6%:67%:50%:50%:40-75%:5% of the corresponding weight basis) and mixture with cement+fly-ash+bottom ash fines+washing aggregate sludge (10%:100%:40-75%:5% of the corresponding weight basis) • Leaching of Cu, Mo, and chloride influenced by the amount of bottom ash fines • Mo leaching influenced by the amount of fly-ash • Chloride leaching influenced by the amount of paper sludge ash	Tang & Brouwers (2017)
Waste material: bottom ash fines (from 20 to 80%), washing aggregate sludge (5%), coal fly-ash (from 5 to 65%), and paper sludge ash (from 5 to 65%) Binder: cement (10%)	• High crushing resistance of the pellets for bottom ash fines addition • Lower cement requirement for pellets production with comparable crushing strength by using bottom ash fines compared only powders • Sulphate and antimony leaching decrease from pellets • Copper leaching increase from pellets	Tang et al. (2017)
Waste material: fluidized bed combustion fly-ash, mine tailing Addition: sodium silicate to form geopolymer aggregates	• Higher crushing force required for the fly-ash geopolymer aggregates compared to lightweight expanded aggregates • Lower crushing force required for the mine tailing geopolymer aggregates compared to lightweight expanded aggregates	Yliniemi et al. (2017)

Waste material: fluxed hematite Binder: modified humic acid or bentonite (in various percentages)	- Wet and dry compression strength increase with increasing dose of modified humic acid - Overall compression strength increase of pellets with modified humic acid at increasing time and temperature of pre-heating and roasting treatments - Lower compression strenght for pre-heated (980 °C, 12 min) and roasted (1250 °C, 10 min) pellets with modified humic (0.6 wt%) compared to pellets with bentonite (0.66 wt%) - Higher mass loss rate of roasted pellets with modified humic acid compared to roasted pellets with bentonite at 980 °C - Lower mass loss rate of roasted pellets with modified humic acid compared to roasted pellets with bentonite at 1100 °C - Comparable mass loss rate values for roasted pellets with modified humic acid compared to roasted pellets with bentonite at 1250 °C	Zhou et al. (2017)
Waste material: fly-ash class C (used alone or in binary mixture from 95 to 85%) Binder: cement (from 5 to 15%) and Ca(OH) ₂ (at 5 or 10%)	- Highest water absorption values of 16.9% for mixture with cement+fly-ash (15%:85%) and 18.46% for mixture with Ca(OH)₂+fly-ash (10%:90%) - Increasing crushing strength up to 10% of cement addition - Lowest crushing strenght value with 15% of cement (299 N) - Crushing strength equal to 470.9 N mixture with Ca(OH)₂+fly-ash (5%:95%) and 285.8 N for mixture with Ca(OH)₂+fly-ash (10%:90%)	Narattha & Chaipanich (2018)
Waste material: fly-ash (from 95 to 80%) Binder: cement (from 5 to 20%) Addition: various replacement level of FA with expandend perlite particles	- Highest aggregates specific strength factor with 20% of cement at 30 rpm and 35° - Aggregate properties improvement with a replacement level of expanded perlite particles up to 40%	Tajra et al. (2018)
Waste material: fly-ash or slag Mixtures: cement+sand, cement+fly-ash+sand, and cement+slag+sand Addition: varying percentage of phase change material for each mixture group (0, 6, 12.5, 25, and 50% for cement+sand mixture while 0, 6, and 12.5% for mixtures with fly-ash or slag)	- Increasing water absorption and permeable porosity with increasing phase change material percentage addition for all the investigated mixtures - Higher crush strength for fly-ash mixture compared to slag mixture with 0, 6, and 12% of phase change material addition - Overall higher crush strength for cement+sand mixtures with comparable phase change material percentages	Tuncel & Pekmezci (2018)

539

540

541

542

543

Table 2. Effects of different operational parameters on cold-bonding pelletization efficiency.

Operational parameter	Main result	Reference
Inclination angle	- Main significant influence on the pelletization efficiency of 414 m² kg⁻¹ fineness fly-ash - Reduced influence on pelletization efficiency of 257 m² kg⁻¹ fineness fly-ash	Manikandan & Ramamurthy (2007)
	- Increasing pelletization efficiency with increasing inclination angle for pellet sizes of 20-12.5 mm and 12.5-10 mm - Increasing pelletization efficiency with decreasing inclination angle for pellet sizes of 10-4.75 mm	Manikandan & Ramamurthy (2009)
	More negligible effect of inclination angle compared to rotation speed and binder content on the pelletization efficiency	Tajra et al. (2018)
Rotation speed	- Main significant influence on the pelletization efficiency of 414 m² kg⁻¹ fineness fly-ash - Reduced influence on pelletization efficiency of 257 m² kg⁻¹ fineness fly-ash - Higher effect of rotation speed compared to the inclination angle	Manikandan & Ramamurthy (2007)
	- Increasing pelletization efficiency with increasing rotation speed for pellet sizes of 20-12.5 mm - Reduced influence on pelletization efficiency for pellets size of 12.5-10 mm - Increasing pelletization efficiency with decreasing rotation speed for pellet sizes of 10-4.75 mm	Manikandan & Ramamurthy (2009)
	- Pellets strength increase with increasing rotation speed up to a certain value (45 rpm) - Lower efficiency for values higher than 45 rpm due to centrifugal force prevalence on gravitational one - Higher effect on pellets crushing strength and pelletization efficiency compared to the inclination angle - Lower effect on pellets crushing strength and pelletization efficiency compared to the binder content	Colangelo & Cioffi (2013) Tajra et al. (2018)
Process duration	- Negligible effect on pelletization efficiency of 414 m² kg⁻¹ fineness fly-ash - More significant effect for 257 m² kg⁻¹ fineness fly-ash with both bentonite or kaolinite content compared to moisture content	Manikandan & Ramamurthy (2007)
	Lower influence on pelletization efficiency for pellet sizes of 20-12.5 mm and 12.5-10 mm than 10-4.75 mm	Manikandan & Ramamurthy (2009)
Binder content	Lower effect compared other parameters	Manikandan & Ramamurthy (2007)
	Higher effect on pelletization efficiency for pellet sizes of 10-4.75 mm than 20-12.5 mm and 12.5-10 mm	Manikandan & Ramamurthy (2009)
	Most influencing parameter on pellets crushing strength and pelletization efficiency compared to the inclination angle and rotation speed	Tajra et al. (2018)

Moisture content	- Negligible effect on pelletization efficiency of 414 m² kg⁻¹ fineness fly-ash - Higher effect for 257 m² kg⁻¹ fineness fly-ash with bentonite or kaolinite content	Manikandan & Ramamurthy (2007)
	Increasing pelletization efficiency with increasing moisture content	Manikandan & Ramamurthy (2009)
	- Improvement of ten percent fines value and reduced water absorption through normal water curing - No significant pellet properties improvement with autoclaving and steam curing compared to the normal water curing	Manikandan & Ramamurthy (2008)

Table 3. Main applications of cold-bonded pellets and related affecting operating conditions.

Main application	Operating condition	Main result	Reference
Lightweight concrete	Aggregate replacement level	- Suitable lightweight concrete characteristics for replacement level ranging between 30-60% - Overall properties worsening for high values of the replacement level	Gesoglu et al. (2004)
	Curing method	Lightweight concrete properties improvement through hot water and steam curing	Gomathi & Sivakumar (2015)
	Mix-design	Bond strength enhancement (65 to 78%) with steel fiber addition (volume ratio ranging from 0.35 to 1.50%)	Güneyisi, Gesoğlu, & Ipek (2013)
		- Compressive strength enhancement with silica fume addition (10%) - Compressive strength enhancement (15-60%) with double-step pelletization for various lightweight aggregates mixtures	Güneyisi, Gesoğlu, Pürsünlü, et al. (2013) Colangelo et al. (2015)
Self-compacting concrete	Aggregate replacement level	Suitable self-compacting concrete properties for GBBS-LWA replacement level up to 100%	Gesoğlu et al. (2012)
		Self-compacting concrete worsening with increasing FA-LWA replacement level from 10 to 50%	Gesoglu et al. (2015)


		Mix-design	Suitable self-compacting concrete properties for 15% LWA replacement level and 5-10% silica fume addition	Güneyisi et al. (2012)
			Optimal H₂O₂ percentage at 7% with resulting LWA suitable for replacement in self-compacting concrete	Hwang & Tran (2015)
			Suitable self-compacting concrete properties with 40% FA-LWA and 5% LECA replacement levels under water-curing	Gopi et al. (2015)
			Compressive and flexural strengths decrease with 30 and 60% LWA replacement level also for LWA with 2.5% of polypropylene fiber or 0.8% of nano-silica	Tang & Brouwers (2018)
Self-compacting mortar	Aggregate replacement level		Self-compacting mortar compressive strength worsening with increasing FA-LWA replacement level (25, 50, 75, and 100%)	Güneyisi, Gesoglu, Ghanim, et al. (2016)
			More noticeable replacement level negative effect on self-compacting mortar compressive strength for increasing water to binder ratio (0.33, 0.37, 0.40, and 0.44)	
			No self-compacting mortar compressive strength decrease with raw bottom ash and expanded shale aggregates replacement level of 25 and 50%	Kim et al. (2016)
			Self-compacting mortar compressive strength decrease by increasing bottom ash-LWA replacement level (at 25 and 50%)	
Adsorbent material	Operating parameters		Adsorption increase with increasing solution pH (100% Cu and Cd adsorption for pH above 9)	Papandreou et al. (2007)
			Adsorption decrease with stirring velocity decrease from 140 to 60 rpm (Cu adsorption decrease from 55 to less than 10%)	
			Adsorption decrease with stirring velocity significant increase (above 140 rpm)	
			Further heavy metals stabilization with adsorbent LWA in concrete at replacement level of 50 and 75%	
			Decreasing concrete compressive strength with replacement level increase	

549


550

551

a)

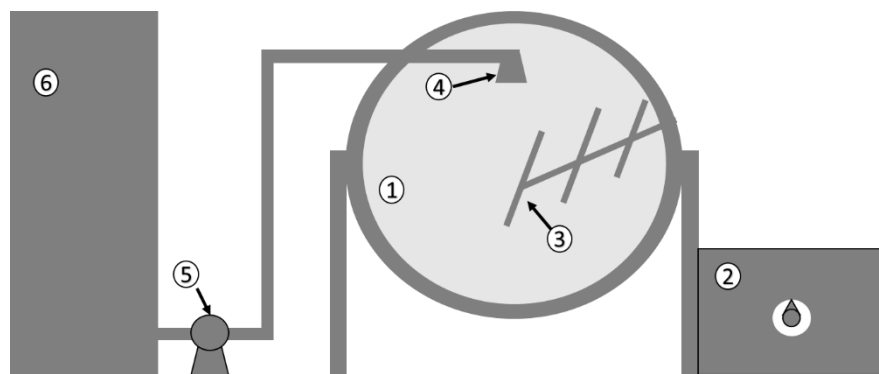

b)

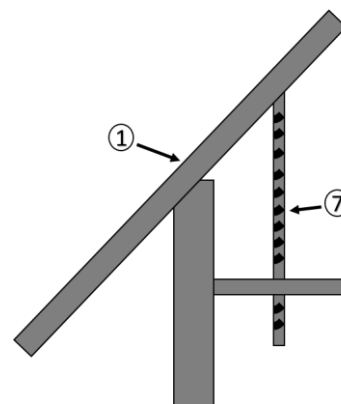


552

553

554

Fig. 1. Schematic representation of the pelletizer a) front section and b) side section; Legend: rotating plate (1), rotation speed controller (2), scrapers (3), nebulizer (4), pump (5), water tank (6), endless screw (7).

555

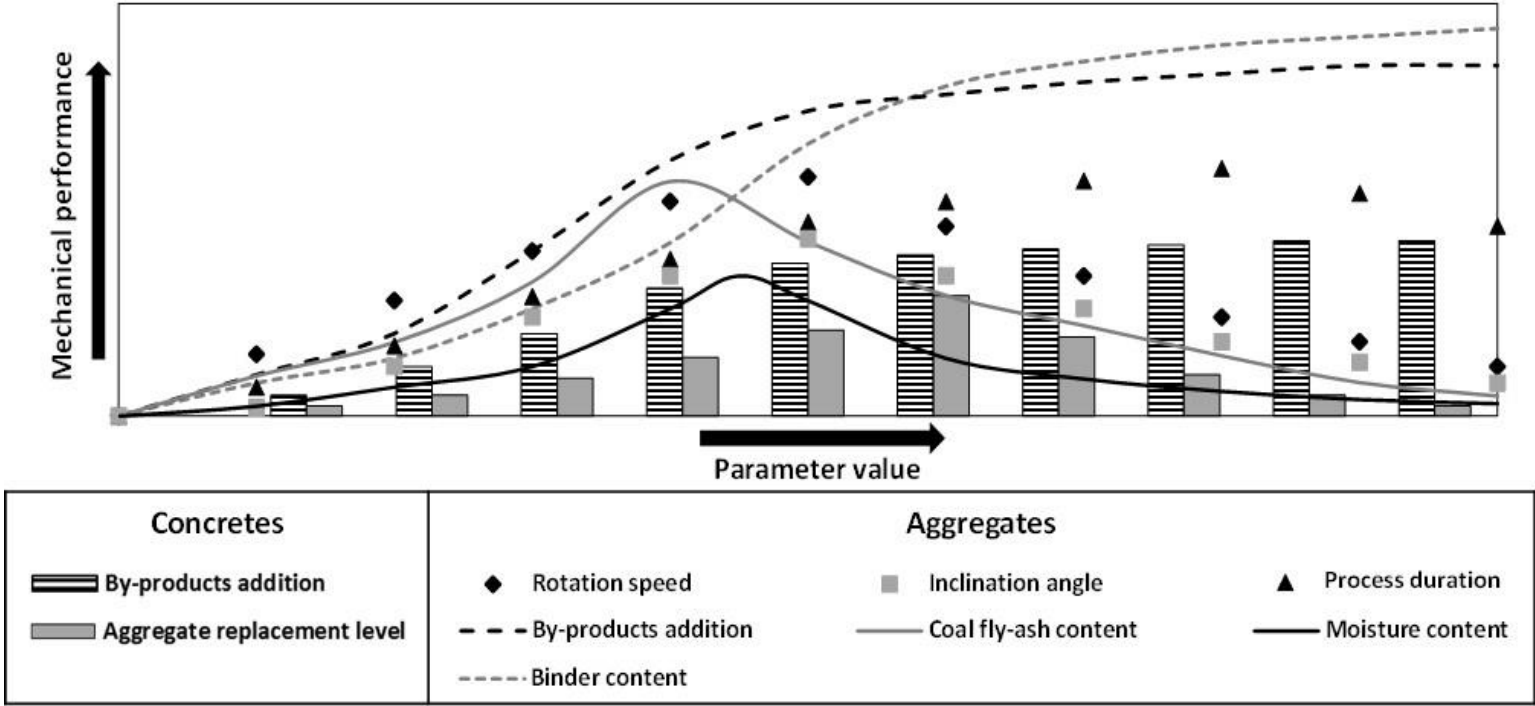

556

557

558

Fig. 2. Exemplifying graphical representation of qualitative variation trends for aggregate (dots and lines) and concrete (histograms) mechanical performance at different values of the operating parameters. Parameter values increase from left to right side and mechanical performance improvement from down to up side.

559

560

References

- Agrawal, B. B., Prasad, K. K., Sarkar, S. B., & Ray, H. S. (2000). Cold bonded ore–coal composite pellets for sponge ironmaking Part 1 Laboratory scale development. *Ironmaking & Steelmaking*, 27(6), 421–425. <https://doi.org/10.1179/030192300677723>
- Amaratunga, L. M. (1995). Cold-bond agglomeration of reactive pyrrhotite tailings for backfill using low cost binders: Gypsum β -hemihydrate and cement. *Minerals Engineering*, 8(12), 1455–1465. [https://doi.org/10.1016/0892-6875\(95\)00110-7](https://doi.org/10.1016/0892-6875(95)00110-7)
- Amaratunga, L. M., & Hmidi, N. (1997). Cold-Bond Agglomeration of Gold Mill Tailings for Backfill Using Gypsum Betahemihydrate and Cement as Low Cost Binders. *Canadian Metallurgical Quarterly*, 36(4), 283–288. <https://doi.org/10.1179/cmqr.1997.36.4.283>
- Aota, J., Morin, L., Zhuang, Q., & Clements, B. (2006). Direct reduced iron production using cold bonded carbon bearing pellets Part 1 – Laboratory metallisation. *Ironmaking & Steelmaking*, 33(5), 426–428. <https://doi.org/10.1179/174328106x118053>
- Arslan, H., & Baykal, G. (2006). Utilization of fly ash as engineering pellet aggregates. *Environmental Geology*, 50(5), 761–770. <https://doi.org/10.1007/s00254-006-0248-7>
- Ayati, B., Ferrándiz-Mas, V., Newport, D., & Cheeseman, C. (2018). Use of clay in the manufacture of lightweight aggregate. *Construction and Building Materials*, 162, 124–131. <https://doi.org/10.1016/J.CONBUILDMAT.2017.12.018>
- Ayati, B., Molineux, C., Newport, D., & Cheeseman, C. (2019). Manufacture and performance of lightweight aggregate from waste drill cuttings. *Journal of Cleaner Production*, 208, 252–260. <https://doi.org/10.1016/J.JCLEPRO.2018.10.134>
- Baykal, G., & Döven, A. G. (2000). Utilization of fly ash by pelletization process; theory, application areas and research results. *Resources, Conservation and Recycling*, 30(1),

584 59–77. [https://doi.org/10.1016/S0921-3449\(00\)00042-2](https://doi.org/10.1016/S0921-3449(00)00042-2)

585 Bui, L. A., Hwang, C., Chen, C., & Hsieh, M. (2012). Characteristics of Cold-Bonded
586 Lightweight Aggregate Produced with Different Mineral Admixtures. *Applied*
587 *Mechanics and Materials*, 174–177, 978–983.
588 <https://doi.org/10.4028/www.scientific.net/amm.174-177.978>

589 Bui, L. A., Hwang, C., Chen, C., Lin, K., & Hsieh, M. (2012). Manufacture and performance
590 of cold bonded lightweight aggregate using alkaline activators for high performance
591 concrete. *Construction and Building Materials*, 35, 1056–1062.
592 <https://doi.org/10.1016/j.conbuildmat.2012.04.032>

593 Çamci, L., Aydin, S., & Arslan, C. (2002). Reduction of iron oxides in solid wastes generated
594 by steelworks. *Turkish Journal of Engineering and Environmental Sciences*, 26(1), 37–
595 44.

596 Cevik, E., Ahlatci, H., & Sun, Y. (2013). Characterization and reduction behavior of cold-
597 bonded composite pellets for direct reduction using an organic binder. *Metallurgist*,
598 57(5–6), 468–477. <https://doi.org/10.1007/s11015-013-9757-2>

599 Chang, T.-P., & Shieh, M.-M. (1996). Fracture properties of lightweight concrete. *Cement*
600 *and Concrete Research*, 26(2), 181–188.

601 Chi, J. M., Huang, R., Yang, C. C., & Chang, J. J. (2003). Effect of aggregate properties on
602 the strength and stiffness of lightweight concrete. *Cement and Concrete Composites*,
603 25(2), 197–205. [https://doi.org/10.1016/S0958-9465\(02\)00020-3](https://doi.org/10.1016/S0958-9465(02)00020-3)

604 Colangelo, F., & Cioffi, R. (2013). Use of cement kiln dust, blast furnace slag and marble
605 sludge in the manufacture of sustainable artificial aggregates by means of cold bonding
606 pelletization. *Materials*, 6(8), 3139–3159. <https://doi.org/10.3390/ma6083139>

- Colangelo, F., Cioffi, R., Montagnaro, F., & Santoro, L. (2012). Soluble salt removal from MSWI fly ash and its stabilization for safer disposal and recovery as road basement material. *Waste Management*, 32(6), 1179–1185.
<https://doi.org/10.1016/j.wasman.2011.12.013>
- Colangelo, F., Messina, F., & Cioffi, R. (2015). Recycling of MSWI fly ash by means of cementitious double step cold bonding pelletization: Technological assessment for the production of lightweight artificial aggregates. *Journal of Hazardous Materials*, 299, 181–191. <https://doi.org/10.1016/J.JHAZMAT.2015.06.018>
- Colangelo, F., Messina, F., Di Palma, L., & Cioffi, R. (2017). Recycling of non-metallic automotive shredder residues and coal fly-ash in cold-bonded aggregates for sustainable concrete. *Composites Part B: Engineering*, 116, 46–52.
<https://doi.org/10.1016/j.compositesb.2017.02.004>
- Dutta, D. K., Bordoloi, D., & Borthakur, P. C. (1997). Investigation on reduction of cement binder in cold bonded pelletization of iron ore fines. *International Journal of Mineral Processing*, 49, 97–105.
- Dutta, D. K., Bordoloi, D., Gupta, S., Borthakur, P. C., Srinivasan, T. M., & Patil, J. B. (1992). Investigation on cold bonded pelletization of iron ore fines using Indian slag-cement. *International Journal of Mineral Processing*, 34, 149–159.
- Ferone, C., Colangelo, F., Messina, F., Iucolano, F., Liguori, B., & Cioffi, R. (2013). Coal combustion wastes reuse in low energy artificial aggregates manufacturing. *Materials*, 6(11), 5000–5015. <https://doi.org/10.3390/ma6115000>
- Ferraro, A., Farina, I., Race, M., Colangelo, F., Cioffi, R., & Fabbicino, M. (2019). Pre-treatments of MSWI fly-ashes: a comprehensive review to determine optimal conditions for their reuse and/or environmentally sustainable disposal. *Reviews in Environmental*

631 *Science and Bio/Technology*, 18(3), 453–471. <https://doi.org/10.1007/s11157-019->
632 09504-1

633 Frankovič, A., Bosiljkov, V. B., & Ducman, V. (2017). Lightweight aggregates made from fly
634 ash using the cold-bond process and their use in lightweight concrete. *Materiali in*
635 *Tehnologije*, 51(2), 267–274. <https://doi.org/10.17222/mit.2015.337>

636 Geetha, S., & Ramamurthy, K. (2010a). Environmental friendly technology of cold-bonded
637 bottom ash aggregate manufacture through chemical activation. *Journal of Cleaner*
638 *Production*, 18(15), 1563–1569. <https://doi.org/10.1016/j.jclepro.2010.06.006>

639 Geetha, S., & Ramamurthy, K. (2010b). Reuse potential of low-calcium bottom ash as
640 aggregate through pelletization. *Waste Management*, 30(8–9), 1528–1535.
641 <https://doi.org/10.1016/j.wasman.2010.03.027>

642 Gesoğlu, M., Güneyisi, E., Ali, B., & Mermerdaş, K. (2013). Strength and transport properties
643 of steam cured and water cured lightweight aggregate concretes. *Construction and*
644 *Building Materials*, 49, 417–424. <https://doi.org/10.1016/j.conbuildmat.2013.08.042>

645 Gesoğlu, M., Güneyisi, E., Alzebaree, R., & Mermerdaş, K. (2013). Effect of silica fume and
646 steel fiber on the mechanical properties of the concretes produced with cold bonded fly
647 ash aggregates. *Construction and Building Materials*, 40, 982–990.
648 <https://doi.org/10.1016/j.conbuildmat.2012.11.074>

649 Gesoğlu, M., Güneyisi, E., Mahmood, S. F., Öz, H. öznur, & Mermerdaş, K. (2012).
650 Recycling ground granulated blast furnace slag as cold bonded artificial aggregate
651 partially used in self-compacting concrete. *Journal of Hazardous Materials*, 235–236,
652 352–358. <https://doi.org/10.1016/j.jhazmat.2012.08.013>

653 Gesoğlu, M., Güneyisi, E., & Öz, H. Ö. (2012). Properties of lightweight aggregates produced

654 with cold-bonding pelletization of fly ash and ground granulated blast furnace slag.
655 *Materials and Structures*, 45(10), 1535–1546. [https://doi.org/10.1617/s11527-012-9855-](https://doi.org/10.1617/s11527-012-9855-9)
656 9

657 Gesoglu, M., Güneyisi, E., Özturan, T., Öz, H. Ö., & Asaad, D. S. (2015). Shear thickening
658 intensity of self-compacting concretes containing rounded lightweight aggregates.
659 *Construction and Building Materials*, 79, 40–47.
660 <https://doi.org/10.1016/j.conbuildmat.2015.01.012>

661 Gesoğlu, M., Güneyisi, E., Özturan, T., Öz, H. Ö., & Asaad, D. S. (2014a). Permeation
662 characteristics of self compacting concrete made with partially substitution of natural
663 aggregates with rounded lightweight aggregates. *Construction and Building Materials*,
664 59, 1–9. <https://doi.org/10.1016/j.conbuildmat.2014.02.031>

665 Gesoğlu, M., Güneyisi, E., Özturan, T., Öz, H. Ö., & Asaad, D. S. (2014b). Self-consolidating
666 characteristics of concrete composites including rounded fine and coarse fly ash
667 lightweight aggregates. *Composites Part B: Engineering*, 60, 757–763.
668 <https://doi.org/10.1016/j.compositesb.2014.01.008>

669 Gesoglu, M., Özturan, T., & Güneyisi, E. (2004). Shrinkage cracking of lightweight concrete
670 made with cold-bonded fly ash aggregates. *Cement and Concrete Research*, 34(7), 1121–
671 1130. <https://doi.org/10.1016/j.cemconres.2003.11.024>

672 Gesoğlu, M., Özturan, T., & Güneyisi, E. (2006). Effects of cold-bonded fly ash aggregate
673 properties on the shrinkage cracking of lightweight concretes. *Cement and Concrete*
674 *Composites*, 28(7), 598–605. <https://doi.org/10.1016/j.cemconcomp.2006.04.002>

675 Gesoğlu, M., Özturan, T., & Güneyisi, E. (2007). Effects of fly ash properties on
676 characteristics of cold-bonded fly ash lightweight aggregates. *Construction and Building*
677 *Materials*, 21(9), 1869–1878. <https://doi.org/10.1016/j.conbuildmat.2006.05.038>

678 Gomathi, P., & Sivakumar, A. (2014). Performance evaluation of alkali activated fly ash
679 lightweight aggregates. *Engineering Journal*, 18(1), 77–85.
680 <https://doi.org/10.4186/ej.2014.18.1.77>

681 Gomathi, P., & Sivakumar, A. (2015). Accelerated curing effects on the mechanical
682 performance of cold bonded and sintered fly ash aggregate concrete. *Construction and*
683 *Building Materials*, 77, 276–287. <https://doi.org/10.1016/j.conbuildmat.2014.12.108>

684 Gopi, R., Revathi, V., & Kanagaraj, D. (2015). Light expanded clay aggregate and fly ash
685 aggregate as self curing agents in self compacting concrete. *Asian Journal of Civil*
686 *Engineering*, 16(7), 1025–1035.

687 Güneyisi, E., Gesoglu, M., Azez, O. A., & Öz, H. Ö. (2015). Physico-mechanical properties
688 of self-compacting concrete containing treated cold-bonded fly ash lightweight
689 aggregates and SiO₂ nano-particles. *Construction and Building Materials*, 101, 1142–
690 1153. <https://doi.org/10.1016/j.conbuildmat.2015.10.117>

691 Güneyisi, E., Gesoglu, M., Azez, O. A., & Öz, H. Ö. (2016). Effect of nano silica on the
692 workability of self-compacting concretes having untreated and surface treated
693 lightweight aggregates. *Construction and Building Materials*, 115, 371–380.
694 <https://doi.org/10.1016/j.conbuildmat.2016.04.055>

695 Güneyisi, E., Gesoğlu, M., & Booya, E. (2012). Fresh properties of self-compacting cold
696 bonded fly ash lightweight aggregate concrete with different mineral admixtures.
697 *Materials and Structures/Materiaux et Constructions*, 45(12), 1849–1859.
698 <https://doi.org/10.1617/s11527-012-9874-6>

699 Güneyisi, E., Gesoğlu, M., Booya, E., & Mermerdaş, K. (2015). Strength and permeability
700 properties of self-compacting concrete with cold bonded fly ash lightweight aggregate.
701 *Construction and Building Materials*, 74, 17–24.

702 <https://doi.org/10.1016/j.conbuildmat.2014.10.032>

703 Güneyisi, E., Gesoglu, M., Ghanim, H., Ipek, S., & Taha, I. (2016). Influence of the artificial
704 lightweight aggregate on fresh properties and compressive strength of the self-
705 compacting mortars. *Construction and Building Materials*, 116, 151–158.
706 <https://doi.org/10.1016/j.conbuildmat.2016.04.140>

707 Güneyisi, E., Gesoğlu, M., & Ipek, S. (2013). Effect of steel fiber addition and aspect ratio on
708 bond strength of cold-bonded fly ash lightweight aggregate concretes. *Construction and*
709 *Building Materials*, 47, 358–365. <https://doi.org/10.1016/j.conbuildmat.2013.05.059>

710 Güneyisi, E., Gesoğlu, M., Mohamadameen, A., Alzebaree, R., Algin, Z., & Mermerdaş, K.
711 (2014). Enhancement of shrinkage behavior of lightweight aggregate concretes by
712 shrinkage reducing admixture and fiber reinforcement. *Construction and Building*
713 *Materials*, 54, 91–98. <https://doi.org/10.1016/j.conbuildmat.2013.12.041>

714 Güneyisi, E., Gesoglu, M., Özturan, T., & Ipek, S. (2015). Fracture behavior and mechanical
715 properties of concrete with artificial lightweight aggregate and steel fiber. *Construction*
716 *and Building Materials*, 84, 156–168. <https://doi.org/10.1016/j.conbuildmat.2015.03.054>

717 Güneyisi, E., Gesoğlu, M., Pürsünlü, Ö., & Mermerdaş, K. (2013). Durability aspect of
718 concretes composed of cold bonded and sintered fly ash lightweight aggregates.
719 *Composites Part B: Engineering*, 53, 258–266.
720 <https://doi.org/10.1016/j.compositesb.2013.04.070>

721 Güneyisi, E., Gesoğlu, M., Altan, I., & Öz, H. Ö. (2015). Utilization of cold bonded fly ash
722 lightweight fine aggregates as a partial substitution of natural fine aggregate in self-
723 compacting mortars. *Construction and Building Materials*, 74, 9–16.
724 <https://doi.org/10.1016/j.conbuildmat.2014.10.021>

725 Gunning, P. J., Hills, C. D., & Carey, P. J. (2009). Production of lightweight aggregate from
 726 industrial waste and carbon dioxide. *Waste Management*, 29(10), 2722–2728.
 727 <https://doi.org/10.1016/j.wasman.2009.05.021>

728 Hapgood, K. P., Iveson, S. M., Litster, J. D., & Liu, L. X. (2007). Chapter 20 Granulation rate
 729 processes. *Handbook of Powder Technology*, 11, 897–977.
 730 [https://doi.org/10.1016/S0167-3785\(07\)80055-8](https://doi.org/10.1016/S0167-3785(07)80055-8)

731 Harikrishnan, K. I., & Ramamurthy, K. (2006). Influence of pelletization process on the
 732 properties of fly ash aggregates. *Waste Management*, 26(8), 846–852.
 733 <https://doi.org/10.1016/j.wasman.2005.10.012>

734 Harilal, B., & Thomas, J. (2013). Concrete made using cold bonded artificial aggregate.
 735 *American Journal of Engineering Research*, 1, 20–25.

736 Hwang, C. L., & Tran, V. A. (2015). A study of the properties of foamed lightweight
 737 aggregate for self-consolidating concrete. *Construction and Building Materials*, 87, 78–
 738 85. <https://doi.org/10.1016/j.conbuildmat.2015.03.108>

739 Joseph, G., & Ramamurthy, K. (2009a). Influence of fly ash on strength and sorption
 740 characteristics of cold-bonded fly ash aggregate concrete. *Construction and Building*
 741 *Materials*, 23(5), 1862–1870. <https://doi.org/10.1016/j.conbuildmat.2008.09.018>

742 Joseph, G., & Ramamurthy, K. (2009b). Workability and strength behaviour of concrete with
 743 cold-bonded fly ash aggregate. *Materials and Structures/Materiaux et Constructions*,
 744 42(2), 151–160. <https://doi.org/10.1617/s11527-008-9374-x>

745 Joseph, G., & Ramamurthy, K. (2011). Autogenous Curing of Cold-Bonded Fly-Ash-
 746 Aggregate Concrete. *Journal of Materials in Civil Engineering*, 23, 393–401.

747 Joseph, N., Harilal, B., Paul, M. M., & Thomas, J. (2013). Strength of cold bonded quarry

748 dust aggregate concrete subjected to high temperatures. *American Journal of*
749 *Engineering Research*, 2, 16–20.

750 Kim, H. K., Ha, K. A., & Lee, H. K. (2016). Internal-curing efficiency of cold-bonded coal
751 bottom ash aggregate for high-strength mortar. *Construction and Building Materials*,
752 126, 1–8. <https://doi.org/10.1016/j.conbuildmat.2016.08.125>

753 Kockal, N. U., & Ozturan, T. (2010). Effects of lightweight fly ash aggregate properties on
754 the behavior of lightweight concretes. *Journal of Hazardous Materials*, 179(1–3), 954–
755 965. <https://doi.org/10.1016/j.jhazmat.2010.03.098>

756 Kockal, N. U., & Ozturan, T. (2011a). Durability of lightweight concretes with lightweight fly
757 ash aggregates. *Construction and Building Materials*, 25(3), 1430–1438.
758 <https://doi.org/10.1016/j.conbuildmat.2010.09.022>

759 Kockal, N. U., & Ozturan, T. (2011b). Strength and elastic properties of structural lightweight
760 concretes. *Materials and Design*, 32(4), 2396–2403.
761 <https://doi.org/10.1016/j.matdes.2010.12.053>

762 Manikandan, R., & Ramamurthy, K. (2007). Influence of fineness of fly ash on the aggregate
763 pelletization process. *Cement and Concrete Composites*, 29(6), 456–464.
764 <https://doi.org/10.1016/j.cemconcomp.2007.01.002>

765 Manikandan, R., & Ramamurthy, K. (2008). Effect of curing method on characteristics of
766 cold bonded fly ash aggregates. *Cement and Concrete Composites*, 30(9), 848–853.
767 <https://doi.org/10.1016/j.cemconcomp.2008.06.006>

768 Manikandan, R., & Ramamurthy, K. (2009). Swelling Characteristic of Bentonite on
769 Pelletization and Properties of Fly Ash Aggregates. *Journal of Materials in Civil*
770 *Engineering*, 21(10), 578–586. [https://doi.org/10.1061/\(asce\)0899-](https://doi.org/10.1061/(asce)0899-)

771 1561(2009)21:10(578)

772 Mantovani, M. C., & Takano, C. (2000). The Strength and the High Temperature Behaviors
 773 of Self-reducing Pellets Containing EAF Dust. *ISIJ International*, 40(3), 224–230.
 774 <https://doi.org/10.2355/isijinternational.40.224>

775 Mantovani, M. C., Takano, C., & Büchler, P. M. (2002). Electric arc furnace dust-coal
 776 composite pellet: effects of pellet size, dust composition, and additives on swelling and
 777 zinc removal. *Ironmaking & Steelmaking*, 29(4), 257–265.
 778 <https://doi.org/10.1179/030192302225004494>

779 McDonald, J. E. D., Roache, S. C., & Kawatra, S. K. (2016). Repurposing mine tailings: Cold
 780 bonding of siliceous iron ore tailings. *Minerals & Metallurgical Processing*, 33(1), 47–
 781 52. <https://doi.org/10.19150/mmp.6467>

782 Narattha, C., & Chaipanich, A. (2018). Phase characterizations, physical properties and
 783 strength of environment-friendly cold-bonded fly ash lightweight aggregates. *Journal of*
 784 *Cleaner Production*, 171, 1094–1100. <https://doi.org/10.1016/j.jclepro.2017.09.259>

785 Nikai, I., & Garbers-Craig, A. M. (2016). Use of Iron Ore Fines in Cold-Bonded Self-
 786 Reducing Composite Pellets. *Mineral Processing and Extractive Metallurgy Review*,
 787 37(1), 42–48. <https://doi.org/10.1080/08827508.2015.1104506>

788 Pal, J., Ghorai, S., Agarwal, S., Nandi, B., Chakraborty, T., Das, G., & Prakash, S. (2015).
 789 Effect of blaine fineness on the quality of hematite iron ore pellets for blast furnace.
 790 *Mineral Processing and Extractive Metallurgy Review*, 36(2), 83–91.
 791 <https://doi.org/10.1080/08827508.2013.873862>

792 Pal, J., Ghorai, S., & Das, A. (2015). Development of carbon composite iron ore micropellets
 793 by using the microfines of iron ore and carbon-bearing materials in iron making.

794 *International Journal of Minerals, Metallurgy and Materials*, 22(2), 132–140.
 795 <https://doi.org/10.1007/s12613-015-1053-7>

796 Papandreou, A., Stournaras, C. J., & Panias, D. (2007). Copper and cadmium adsorption on
 797 pellets made from fired coal fly ash. *Journal of Hazardous Materials*, 148(3), 538–547.
 798 <https://doi.org/10.1016/j.jhazmat.2007.03.020>

799 Patel, J. kumar, Patil, H., Patil, Y., & Vesmawala, G. (2018). Production and performance of
 800 alkali-activated cold-bonded lightweight aggregate in concrete. *Journal of Building*
 801 *Engineering*, 20(February), 616–623. <https://doi.org/10.1016/j.jobbe.2018.09.012>

802 Polowczyk, I., Bastrzyk, A., Koźlecki, T., Rudnicki, P., Sawiński, W., Sadowski, Z., &
 803 Sokołowski, A. (2007). Application of fly ash agglomerates in the sorption of arsenic.
 804 *Polish Journal of Chemical Technology*, 9(2), 37–41. [https://doi.org/10.2478/v10026-](https://doi.org/10.2478/v10026-007-0022-y)
 805 [007-0022-y](https://doi.org/10.2478/v10026-007-0022-y)

806 Rivera, F., Martínez, P., Castro, J., & López, M. (2015). Massive volume fly-ash concrete: A
 807 more sustainable material with fly ash replacing cement and aggregates. *Cement and*
 808 *Concrete Composites*, 63, 104–112. <https://doi.org/10.1016/j.cemconcomp.2015.08.001>

809 Robinson, R. (2005). High temperature properties of by-product cold bonded pellets
 810 containing blast furnace flue dust. *Thermochimica Acta*, 432(1), 112–123.
 811 <https://doi.org/10.1016/j.tca.2005.04.015>

812 Sah, R., & Dutta, S. K. (2010). Effects of binder on the properties of iron ore-coal composite
 813 pellets. *Mineral Processing and Extractive Metallurgy Review*, 31(2), 73–85.
 814 <https://doi.org/10.1080/08827500903404732>

815 Senneca, O., Cortese, L., Di Martino, R., Fabbicino, M., Ferraro, A., Race, M., & Scopino,
 816 A. (2020). Mechanisms affecting the delayed efficiency of cement based

817 stabilization/solidification processes. *Journal of Cleaner Production*, 261, 121230.
818 <https://doi.org/10.1016/j.jclepro.2020.121230>

819 Tajra, F., Elrahman, M. A., Chung, S. Y., & Stephan, D. (2018). Performance assessment of
820 core-shell structured lightweight aggregate produced by cold bonding pelletization
821 process. *Construction and Building Materials*, 179, 220–231.
822 <https://doi.org/10.1016/j.conbuildmat.2018.05.237>

823 Tang, P., & Brouwers, H. J. H. (2017). Integral recycling of municipal solid waste
824 incineration (MSWI) bottom ash fines (0–2 mm) and industrial powder wastes by cold-
825 bonding pelletization. *Waste Management*, 62, 125–138.
826 <https://doi.org/10.1016/j.wasman.2017.02.028>

827 Tang, P., & Brouwers, H. J. H. (2018). The durability and environmental properties of self-
828 compacting concrete incorporating cold bonded lightweight aggregates produced from
829 combined industrial solid wastes. *Construction and Building Materials*, 167, 271–285.
830 <https://doi.org/10.1016/j.conbuildmat.2018.02.035>

831 Tang, P., Florea, M. V. A., & Brouwers, H. J. H. (2017). Employing cold bonded pelletization
832 to produce lightweight aggregates from incineration fine bottom ash. *Journal of Cleaner*
833 *Production*, 165, 1371–1384. <https://doi.org/10.1016/j.jclepro.2017.07.234>

834 Terzić, A., Pezo, L., Mitić, V., & Radojević, Z. (2015). Artificial fly ash based aggregates
835 properties influence on lightweight concrete performances. *Ceramics International*, 41,
836 2714–2726. <https://doi.org/10.1016/j.ceramint.2014.10.086>

837 Thomas, J., & Harilal, B. (2015). Properties of cold bonded quarry dust coarse aggregates and
838 its use in concrete. *Cement and Concrete Composites*, 62, 67–75.
839 <https://doi.org/10.1016/j.cemconcomp.2015.05.005>

840 Thomas, J., & Harilal, B. (2016). Mechanical properties of cold bonded quarry dust aggregate
 841 concrete subjected to elevated temperature. *Construction and Building Materials*, 125,
 842 724–730. <https://doi.org/10.1016/j.conbuildmat.2016.08.093>

843 Tuncel, E. Y., & Pekmezci, B. Y. (2018). A sustainable cold bonded lightweight PCM
 844 aggregate production: Its effects on concrete properties. *Construction and Building*
 845 *Materials*, 181, 199–216. <https://doi.org/10.1016/j.conbuildmat.2018.05.269>

846 Vasugi, V., & Ramamurthy, K. (2014). Identification of design parameters influencing
 847 manufacture and properties of cold-bonded pond ash aggregate. *Materials and Design*,
 848 54, 264–278. <https://doi.org/10.1016/j.matdes.2013.08.019>

849 Velis, C. A., Franco-Salinas, C., Osullivan, C., Najorka, J., Boccaccini, A. R., & Cheeseman,
 850 C. R. (2014). Up-cycling waste glass to minimal water adsorption/absorption lightweight
 851 aggregate by rapid low temperature sintering: Optimization by dual process-mixture
 852 response surface methodology. *Environmental Science and Technology*, 48(13), 7527–
 853 7535. <https://doi.org/10.1021/es5003499>

854 Vijay, P., & Singh, S. (2014). Physical and Mechanical Properties of Steel Fiber Reinforced
 855 Lightweight Aggregate Concrete Using Fly Ash. *International Journal of Emerging*
 856 *Technology and Advanced Engineering*, 4(10), 596–601.

857 Yliniemi, J., Nugteren, H., Illikainen, M., Tiainen, M., Weststrate, R., & Niinimäki, J. (2016).
 858 Lightweight aggregates produced by granulation of peat-wood fly ash with alkali
 859 activator. *International Journal of Mineral Processing*, 149, 42–49.
 860 <https://doi.org/10.1016/j.minpro.2016.02.006>

861 Yliniemi, J., Pesonen, J., Tanskanen, P., Peltosaari, O., Tiainen, M., Nugteren, H., &
 862 Illikainen, M. (2016). Alkali Activation–Granulation of Hazardous Fluidized Bed
 863 Combustion Fly Ashes. *Waste and Biomass Valorization*, 8(2), 339–348.

<https://doi.org/10.1007/s12649-016-9580-7>

Yliniemi, J., Tiainen, M., & Illikainen, M. (2016). Microstructure and Physical Properties of Lightweight Aggregates Produced by Alkali Activation-High Shear Granulation of FBC Recovered Fuel-Biofuel Fly Ash. *Waste and Biomass Valorization*, 7(5), 1235–1244. <https://doi.org/10.1007/s12649-016-9509-1>

Yliniemi, Paiva, Ferreira, Tiainen, & Illikainen. (2017). Development and incorporation of lightweight waste-based geopolymer aggregates in mortar and concrete. *Construction and Building Materials*, 131, 784–792. <https://doi.org/10.1016/j.conbuildmat.2016.11.017>

Zhou, Y., Wattanaphan, P., & Kawatra, S. K. (2017). Application of Modified Humic Acid (MHA) Binder in the Pelletizing Of Fluxed Hematite Concentrate. *Mineral Processing and Extractive Metallurgy Review*, 38(2), 126–131. <https://doi.org/10.1080/08827508.2017.1281132>