Femtosecond Laser Directed Fabrication of Optical Diffusers

Tawfiq Alqurashi[1,2], Aydin Sabouri [1], Pavel Penchev [1], Rayan M. Ameen [3], Ali K. Yetisen[4], Stefan Dimov[1], and Haider Butt[1,]*

[1]School of Engineering, University of Birmingham, Birmingham, B15 2TT, UK

[2]Department of Mechanical Engineering, School of Engineering, Shaqra University, Dawadmi, Saudi Arabia

[3]School of Metallurgy and Materials, University of Birmingham, Birmingham, B15 2TT, UK

[4]Harvard-MIT Division of Health Sciences and Technology, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA

Keywords: Femtosecond laser ablation, optical diffusers, nanopatterning, nanoparticles

Abstract

Optical diffusers are widely used in filament lamps, imaging systems, display technologies, lasers, and Light Emitting Diodes (LEDs). Here, a method for the fabrication of optical diffusers through femtosecond laser machining is demonstrated. Float glass surfaces were ablated with femtosecond laser light to form nanoscale ripples with dimensions comparable to the wavelength of visible light. These structures produce highly efficient and wide field of view diffusers. The machined patterns altered the average surface roughness (Ra) in the range from 375 to 424 nm. The optical diffusion characteristic and a maximum diffusion angle of near 172˚ was achieved with optimum machining parameters. The transmission performance of the diffusers was measured to be ~30% across the visible spectrum. The demonstrated technique has potential for producing low-cost large area optical devices. The process benefits from the flexibility of the laser writing method and enables the production of custom holographic diffusers.

Introduction

Optical diffusers are widely used in a myriad of optical devices including liquid crystal displays (LCDs), light-emitting diodes (LEDs), light sources, and lasers [1, 2]. Optical diffusers may consist of incorporated particles or the microstructured surface-relief patterns [3, 4]. The most widely used surface-relief structures include microlenses [5], pyramids, [6] and textured surfaces [7, 8]. Applications of these types of diffusers can be found in filament lamps [9], LEDs [10] and fiber optics [11]. Fabrication of textured surfaces through femtosecond (FS) laser ablation is a rapidly growing area of interest [12-14]. This fast and potentially viable method can produce micro- and nano-scale ripples on substrate surfaces to change their physical properties [15-17]. Such surface texturing alters optical reflection/ transmission properties [18].

Here, we report the development of glass-based optical diffusers via FS laser patterning. FS laser ablation was used to produce both nano- and microstructures (~20 μm) to increasing the roughness of the glass surfaces, which randomly diffused the transmitted light. Optical scattering from the textured glasses substrate was examined by angle-resolved spectral measurements. The optical response was characterized in the visible spectrum.

Femtosecond Laser Writing of Glass Diffusers

Float glass slides were textured using an in house FS laser microprocessing platform. The surface structures on glass substrates were produced by controlling the polarization and hatch directions of the laser beam. Figure 1a shows the schematic of the laser machining

setup that includes an ultrashort ytterbium-doped fiber laser (0.8 W, 1030 nm, 310 fs, 100 kHz), a telecentric lens with a focal length of 10.0 cm and a 3D optical beam deflection system for dynamically scanning surfaces. The working envelope defined by the scan head and the focusing lens was 35 mm (x) × 35 mm (y) × 6 mm (z). Furthermore, the focal beam spot diameter was ~30 µm. The glass substrate was scanned at a speed of 200 mm s^{-1} with a hatch distance of 4 µm while the pulse energy was 8 µJ. Figure 1(b) shows a typical surface morphology resulting on the substrate after the FS laser processing.

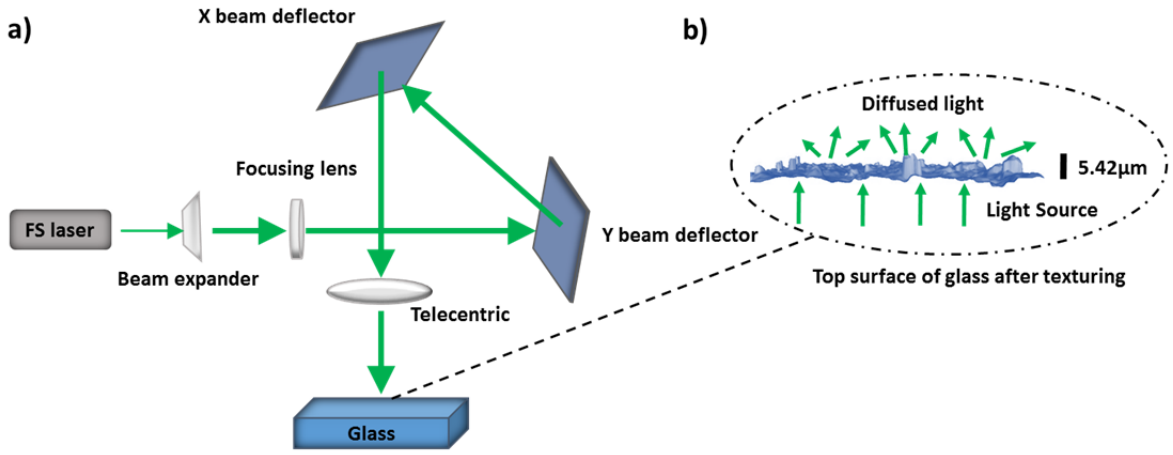


Figure 1. Fabrication of optical diffusers via FS laser patterning. (a) Schematic of the laser setup. (b) Textured surface and the resulting light diffusion.

Laser parameters were varied to pattern glass substrates (Figure 2). The surface morphology of textured glass was analyzed by an optical microscope and average roughness (Ra) was measured using Alicona G5 Infinite Focus (IF) system. In Figure 2a-c, the samples represented by h1-3 were textured using circular polarization with varying hatch directions: horizontal, vertical and at 45°, respectively. Figure 2a-c shows the surface roughness of the fabricated diffusers along with the cross-sectional images. Side views of diffusers illustrate the difference in the surface topography produced by various

laser processing parameters (hatch direction, polarization). The morphologies and arrangements of both nano- and microscale structures were dependent on the FS laser processing settings such as hatch direction [15, 19]. Figure S1 shows the 3D map of the fabricated nanoripples.

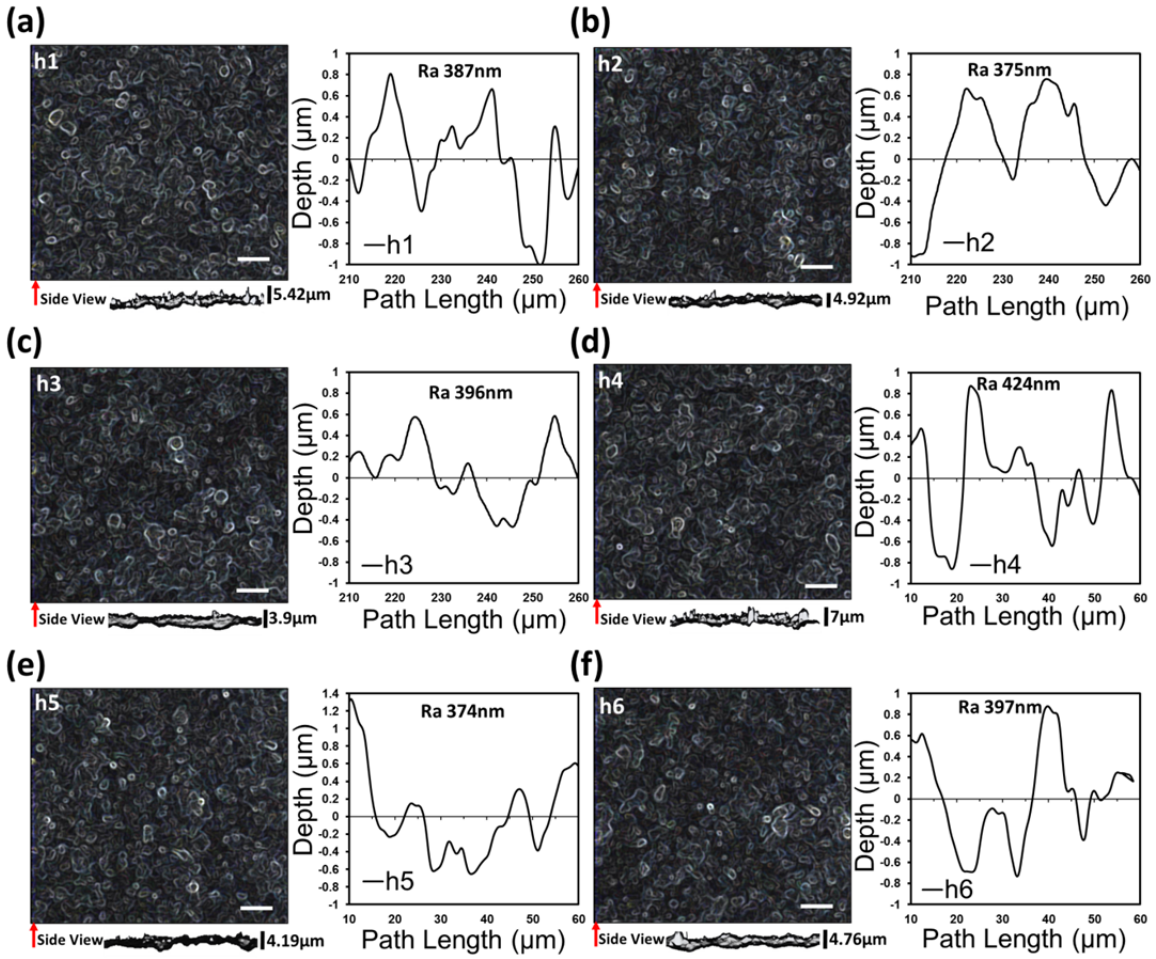


Figure 2. Femtosecond laser patterning of glass diffusers. Microscopic images from the top and side views of the microstructured ripples and corresponding surface roughnesses. (a-c) Samples from h1 to h3 were textured by using circular polarization with three different hatch direction, *i.e.* horizontal, vertical and at 45˚, while the polarization was changed to linear for (d-f) samples from h4 to h6.

Another set of samples (h4-6) were produced by changing the laser polarization to linear (Figure 2d-f). The size and number of surface structures were reduced when the hatch direction was vertical. In general, the surface structures on all samples had non-uniform overlaps. The average surface roughness was between 375 to 424 nm (Figure 2). The vertical hatch direction produced the lowest average roughness of 375 and 374 nm for samples h2 and h5, respectively.

Additionally, the fabricated nano- and microstructures were imaged by a scanning electron microscope (SEM) (Figure 3). Glass samples were coated with gold layer (5-10 nm). The SEM imaging was performed with a field emission gun (FEG) at 10 kV. The nano and microripples were fabricated by overlapping of multiple laser passes. The arrangements of structures produced were highly dependent on the hatch direction (Figure 3). The high magnification images revealed that the fabrication process produced nanoparticles on ripples in the order of few hundred nanometres. These surface structures scatters light [20].

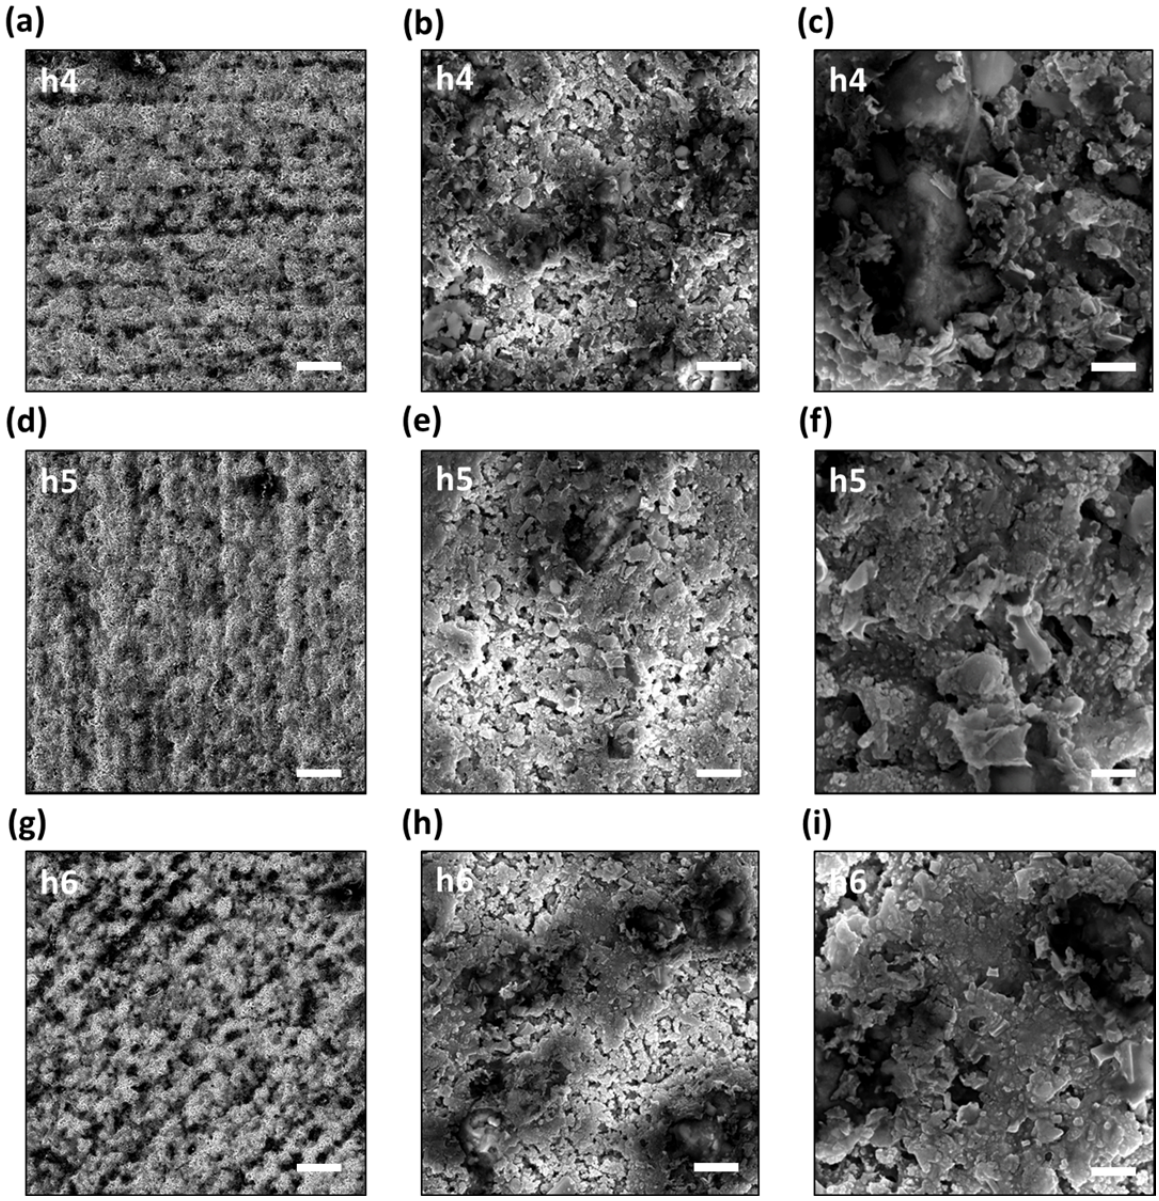


Figure 3. SEM microscopy of the laser-patterned nanoripples (h4 and h6). (a, d, g) 1000× magnification. Scale bar= 25 μm. (b, e, h) 20,000× magnification. Scale bar 2.5 μm (g, h, i) 35,000 magnification Scale bar = 1 μm.

Characterization of Optical Diffusers

The samples were examined by angle-resolved optical power intensity measurements and spectroscopy analyses. The angular measurement setup consisted of a computer-controlled rotation stage, laser sources (λ= 633, 533, and 450 nm), and an optical powermeter (Figure 4a). The diffuser samples were rotated with 1° increments. To reduce the stray light effect, a cylindrical tube was placed in front of the detector of the powermeter. The distances between the laser source-sample and sample-detector were 3 and 13 cm, respectively. The sample was rotated from -90° to +90° from the normal incident (Figure 4b). The motorized stage was controlled by a software that recorded the powermeter readings at each angle simultaneously.

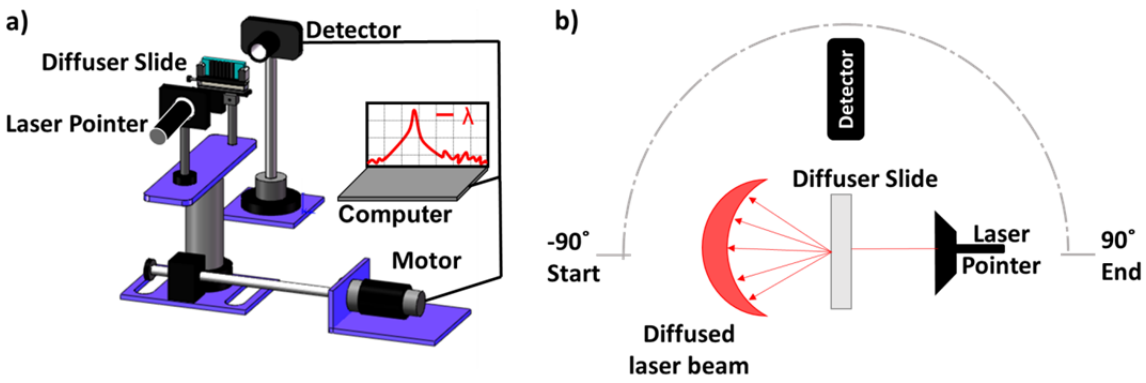


Figure 4. Angle-resolved spectral measurement setup for the analysis of optical diffusers. (a) Schematic of the experimental setup. (b) Top view of the experimental setup.

Figure 5a-d shows the angle-resolved measurements of transmitted diffused light. In Figure 5a-b, measurements were performed on samples with circular and vertical polarization using a red laser beam. Figure 5c-d shows the diffusion measurements using green and blue laser beams. The surface features produced on glass surfaces were

randomly distributed causing the diffusion of light in wide angles. According to Bragg law the large diffusion angles suggest that the structures are of the same scale as the wavelength of light (few hundred nanometres). Due to the random distribution of surface structures, the mean surface roughness measurements revealed that the surface features overlapped and formed on each other, which affected the properties of the diffusion angles. The measured diffusion angle varied from 152° to 172°. Figure 5a-b shows a wide diffusion angle (~172°) with a peak transmission intensity (~1.1%) at 0°. Figure 5a shows that the normal transmission intensities for h1-3 were 0.5, 0.85 and 0.8% and the diffusions angles were 154°, 170° and 166°, respectively. The samples created with linear polarization (h4-6) displayed slightly higher transmission intensities (~0.054%). Meanwhile, the diffusion angle decreased by ~8˚ for samples h4 and h5. This signifies that the structures produced with linear polarization had larger lateral dimensions and lower spatial density, which led to narrower diffusion field of view and more light being focused near 0°, the diffusion properties of the samples were also analyzed using 450 and 533 nm laser beams. The samples displayed higher optical transmission for these two wavelengths (2.2% for 533 nm and 1.35% for 450 nm); however, the light scattering to higher angles was lower, 144° for 533 nm and 152° for 450 nm. Additionally, Figure 5a-d shows the full width at half maximum (FWHM) for the diffusion plots. The highest FWHM were recorded in response to the red light; however, the intensity peak was the lowest as compared to other wavelengths. The reason being that the light was three dimensionally diffused at larger angles, hence reducing the light focused near zero degrees.

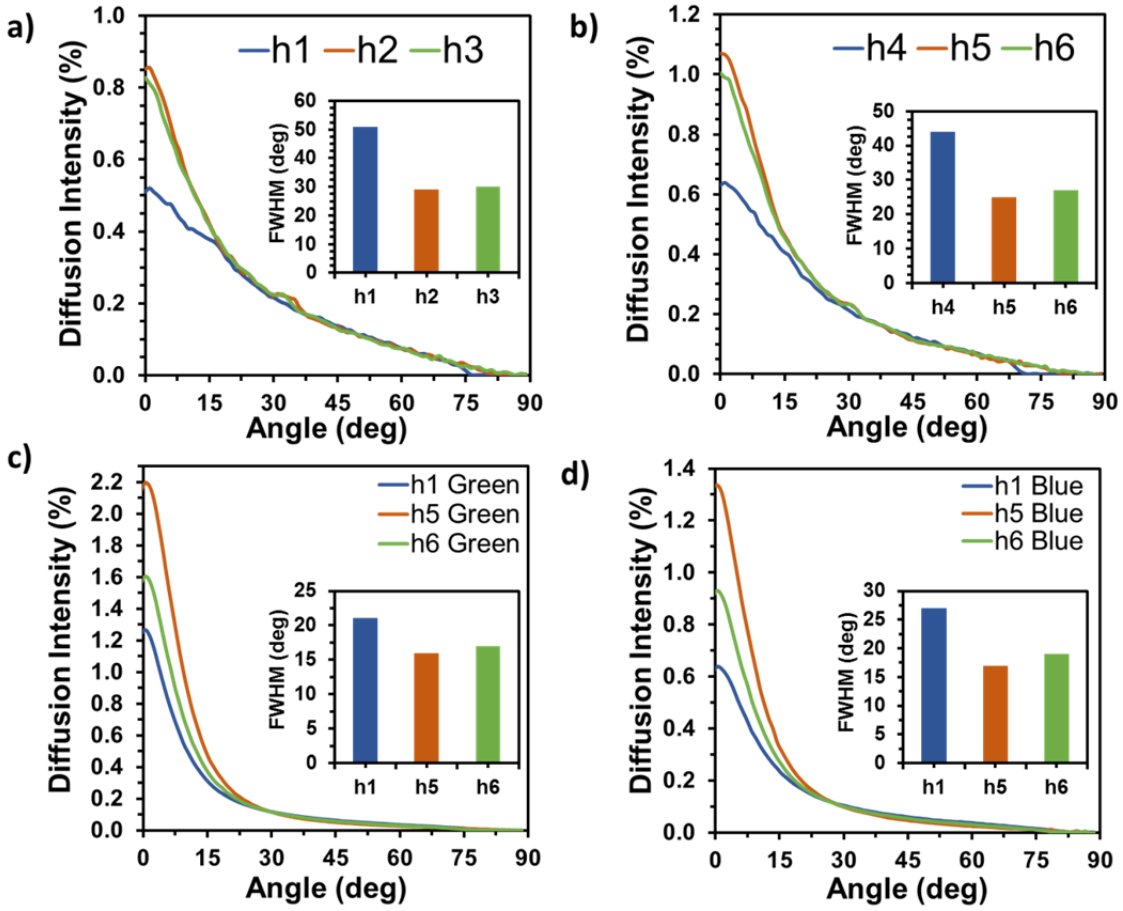


Figure 5. Angule-resolved measurements of the optical diffusers. (a-b) h1-6 samples using 633 nm laser beam. The insets show the full width half maxima. The diffusion in response to (c) 533 nm and (d) 450 nm laser beams.

In practical applications, diffusers are generally used for scattering white light. Hence, optical reflection and transmission measurements were also conducted using broadband light. These measurements were performed by using a spectrophotometer (2 nm resolution), which was connected to an optical microscope through an optical fiber. Figure 6 shows the measured average reflection and transmission spectra. In general, the surface features reduced most of the light transmittance with haze boosting effects [21]. The results show that ~40% of the light was transmitted through the optical diffusers at 400 nm, and it sharply reduced to 20% at 475 nm (Figure 6a-b). However, the

transmission intensities gradually increased from 20% to 30% between 500 nm to 700 nm. The reflection measurements showed that ~55% of the light was back-scattered from the textured surfaces at 400 nm and it reduced to 10% at 500 nm (Figure 6c-d). For larger wavelengths, the transmission remained stable until it reached 670 nm and then increased to 27% at 700 nm. In general, the transmission and reflection measurements through the microscope setup had higher efficiency as compared to the angle-resolved measurements. This was due to the fact the microscope objectives (due to high numerical aperture) received and focussed much more light (including the diffused light) coming from the samples.

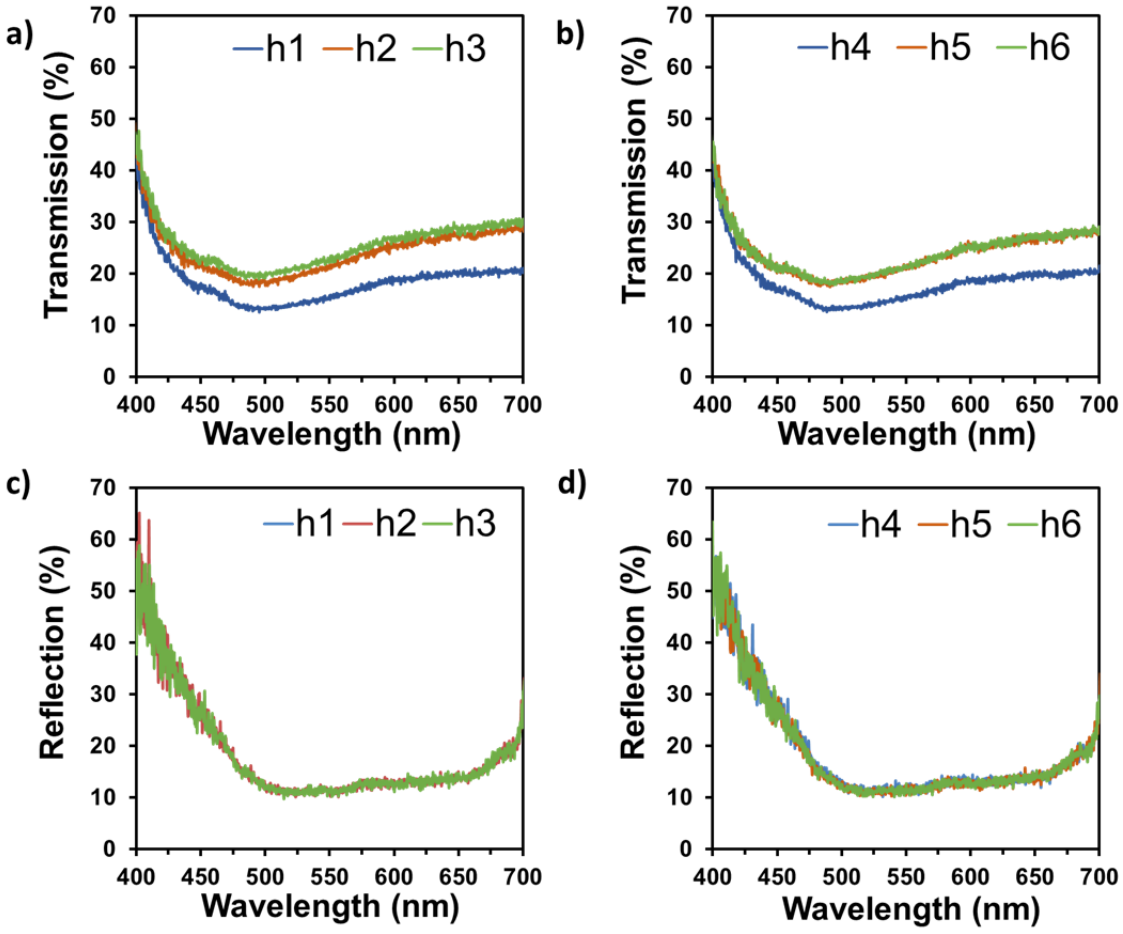


Figure 6. Spectroscopic measurements of the optical diffusers using broadband light. (a-b) Transmission and (c-d) reflection modes.

To visualize the three-dimensional distribution of the diffused light, the diffusers were located at the centre of a semi-transparent globe and the laser source was positioned below it (Figure 7a-c). Figure 7b shows photographs of the laser lights at 450, 533 and 633 nm without an optical diffuser. When the laser beams were transmitted through the optical diffusers, the light was scattered at large angles (Figure 7d). The field view of optical diffusion increased from blue to red beams. This is in agreement with the Bragg law, [22, 23] which states that the diffraction angles increases for the increase in incident wavelength. Our approach showed higher angle scattering as compared to other optical diffusers and the fabrication is amenable to mass manufacturing due to rapid laser writing, and accurate pattering of glass substrates [2, 4, 24]

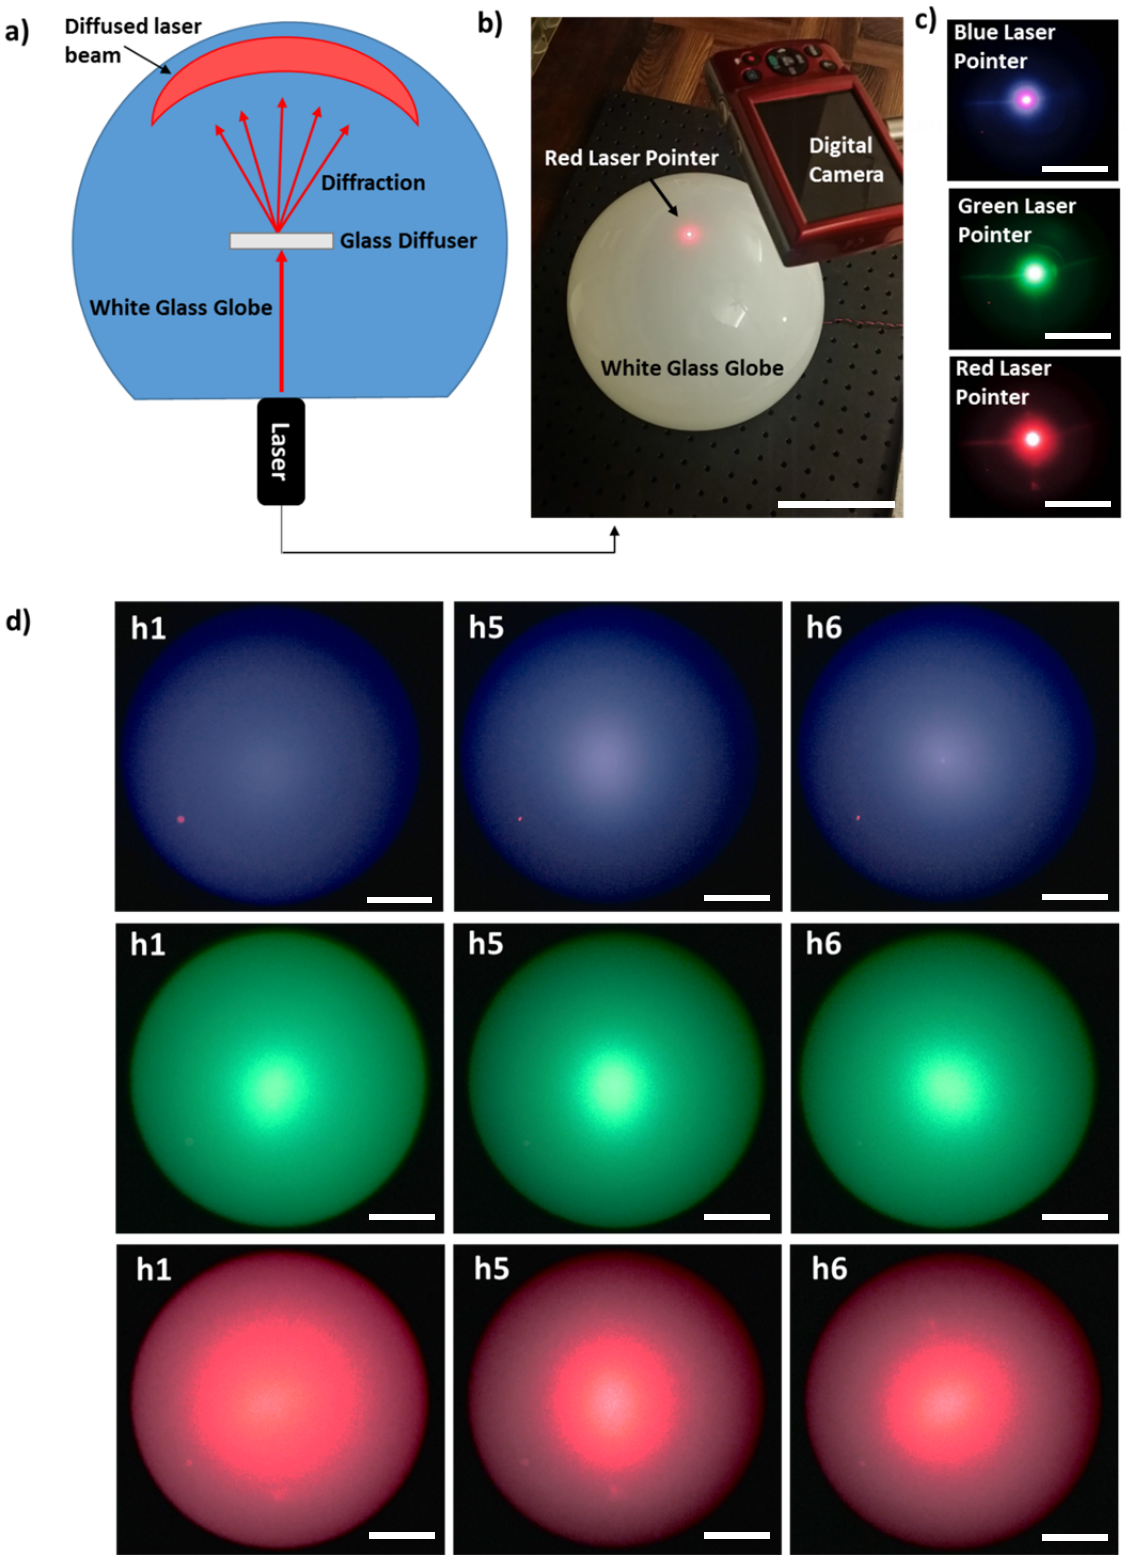


Figure 7. Visualization of the optical diffusion under a semi-transparent white glass globe. (a) Schematic of experimental setup used to capture the speckle patterns from the optical diffusers. (b) A photograph of experimental setup. Scale bar= 12 cm. (c) 450, 550

and 700 nm beams illuminating the glass globe without a diffuser. Scale bar= 12 cm (d) Laser beams were passed through the diffusers producing different speckle patterns and intensities. Scale bar= 6 cm.

Conclusion

We have developed a cost effective method for fabricating optical diffusers by using femtosecond laser ablation. The laser machining nano and microscale surface structures on the float glass increased the diffusion angle up to ~172° and reduced light normal transmittance. The effects of hatch direction and laser polarization on transmission characteristics of the diffusers were also investigated. The maximum and minimum transmission intensities were at 400 and 475 nm, respectively. The fabrication method developed in this work has fast processing time and flexibility of patterning various geometries. Optical diffusers produce by this method may have applications in photonic communication systems, displays, and LEDs.

ASSOCIATED CONTENT

AUTHOR INFORMATION

Corresponding Author

* h.butt@bham.ac.uk

Author Contributions

H.B. conceived the idea. T.A., A.S, P.P, and H.B. performed the experiments. R.M.A performed SEM imaging. T.A., A.K.Y, and H.B wrote the article.

Notes

We declare no competing financial interests.

References

1. Hu, J., et al., *Novel multifunctional microspheres of polysiloxane@CeO2-PMMA: Optical properties and their application in optical diffusers.* Optical Materials, 2013. **36**(2): p. 271-277.
2. Huang, T.-C., et al., *Fast fabrication of integrated surface-relief and particle-diffusing plastic diffuser by use of a hybrid extrusion roller embossing process.* Optics Express, 2008. **16**(1): p. 440-447.
3. Knowles, K.M., et al., *Light scattering and optical diffusion from willemite spherulites.* Optical Materials, 2016. **52**: p. 163-172.
4. Butt, H., et al., *Devitrite-Based Optical Diffusers.* ACS Nano, 2014. **8**(3): p. 2929-2935.
5. Wu, C.Y., T.H. Chiang, and C.C. Hsu, *Fabrication of microlens array diffuser films with controllable haze distribution by combination of breath figures and replica molding methods.* Optics Express, 2008. **16**(24): p. 19978-19986.
6. Chang, S.I., et al., *Microlens array diffuser for a light-emitting diode backlight system.* Optics Letters, 2006. **31**(20): p. 3016-3018.
7. Lin, L., T.K. Shia, and C.J. Chiu, *Silicon-processed plastic micropyramids for brightness enhancement applications.* Journal of Micromechanics and Microengineering, 2000. **10**(3): p. 395-400.
8. Yeh, S.L., *A study of light scattered by surface-relief holographic diffusers.* Optics Communications, 2006. **264**(1): p. 1-8.
9. Allen, G.R., et al., *Led lamp with diffuser having spheroid geometry*. 2013, US20130201680 A1.
10. Uehran, R.S., *LED lighted sign with a light diffuser*. 2004, US6829852 B1.
11. *Improved LED car lamp*. 2014, CN203404700 U.

12. Han, Y., X. Zhao, and S. Qu, *Polarization dependent ripples induced by femtosecond laser on dense flint (ZF6) glass.* Optics Express, 2011. **19**(20): p. 19150-19155.
13. Tomita, T., et al., *Effect of surface roughening on femtosecond laser-induced ripple structures.* Applied Physics Letters, 2007. **90**(15): p. 153115.
14. Sugioka, K. and Y. Cheng, *Ultrafast lasers[mdash]reliable tools for advanced materials processing.* Light Sci Appl, 2014. **3**: p. e149.
15. Han, W., et al., *Continuous modulations of femtosecond laser-induced periodic surface structures and scanned line-widths on silicon by polarization changes.* Optics Express, 2013. **21**(13): p. 15505-15513.
16. Wang, H., et al., *Femtosecond laser-induced simultaneous surface texturing and crystallization of a-Si:H thin film: morphology study.* The International Journal of Advanced Manufacturing Technology, 2013. **65**(9): p. 1691-1703.
17. Gattass, R.R. and E. Mazur, *Femtosecond laser micromachining in transparent materials.* Nat Photon, 2008. **2**(4): p. 219-225.
18. Brown, M.S. and C.B. Arnold, *Fundamentals of Laser-Material Interaction and Application to Multiscale Surface Modification*, in *Laser Precision Microfabrication*, K. Sugioka, M. Meunier, and A. Piqué, Editors. 2010, Springer Berlin Heidelberg: Berlin, Heidelberg. p. 91-120.
19. Chen, J.-T., et al., *Laser-induced periodic structures for light extraction efficiency enhancement of GaN-based light emitting diodes.* Optics Express, 2012. **20**(5): p. 5689-5695.
20. *On the Scattering of Light by small Particles*, in *Scientific Papers:*. 2009, Cambridge University Press. p. 104-110.
21. Cho, D.-H., et al., *Light diffusing effects of nano and micro-structures on OLED with microcavity.* Optics Express, 2014. **22**(S6): p. A1507-A1518.
22. Butt, H., et al., *Carbon Nanotube Based High Resolution Holograms.* Advanced Materials, 2012. **24**(44): p. OP331-OP336.
23. Butt, H., et al., *Visible Diffraction from Graphene and Its Application in Holograms.* Advanced Optical Materials, 2013. **1**(11): p. 869-874.
24. Bitterli, R., et al. *Refractive statistical concave 1D diffusers for laser beam shaping*. 2008.